



# IJRASET

International Journal For Research in  
Applied Science and Engineering Technology



---

# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

---

**Volume:** 10    **Issue:** VIII    **Month of publication:** August 2022

**DOI:** <https://doi.org/10.22214/ijraset.2022.46417>

[www.ijraset.com](http://www.ijraset.com)

Call:  08813907089

E-mail ID: [ijraset@gmail.com](mailto:ijraset@gmail.com)

# Experimental Study of the Physical Properties of Concrete Prepared by Partial Replacement of Cement with Alccofine, Metakaolite and GGBS

Nayyer Ansari<sup>1</sup>, Deepak Kumar Bandewar<sup>2</sup>

SIRTS

**Abstract:** Cement concrete is the most broadly used construction material in the world. Maintenance and repair work of concrete structures is an increasing problem involving the significant expenditure. As a result of study carried out worldwide, it has been made possible to process the material to satisfy more strong performance requirements, especially durability. To reduce the expenditure for making of concrete we should consider the industrial waste materials for partial replacement of cement with supplementary cementitious materials like alccofine, GGBS and meta-kaoline. We consider these materials because these are available at very low cost. For this purpose we prepared number of samples by the various mixes with variable percentage of these materials in the mix. After the selection of the mix on these prepared specimens we perform workability and compressive strength test in the laboratory. By these tests we come to know that when we replace cement by Alccofine up to 10% the compressive strength increases 414.53 but after this range of addition it starts reducing the strength. when we replace cement by GGBS up to 15% the compressive strength increases 421.40 but after this range of addition it starts reducing the strength and same when we replace cement by Meta-kaoline up to 10% the compressive strength increases 448.44 but after this range of addition it starts reducing the strength

**Keywords:** Alccofine, GGBS, Meta-kaoline, Compressive strength, workability.

## I. INTRODUCTION

### A. Conventional Concrete

Concrete is most widely used construction material in the world. Concrete is a composite material formed by the combination of (a) cement, (b) aggregate and (c) water in particular proportion in such way that concrete produce meets the need of the job on hand particularly as regards its workability, strength, durability and economy. In our country the concrete is generally prepared at the sites and therefore need to be carefully supervised and controlled in order that it performs the way its technically expected to perform. Lot of care is to be taken in every stage of manufacturing of concrete.

The various stages of manufacturing concrete are:

- 1) Batching
- 2) Mixing
- 3) Transporting
- 4) Placing
- 5) Compacting
- 6) Curing
- 7) Finishing

### B. Special Concrete

#### 1) Fibre Reinforced Concrete

Fibre reinforced concrete (FRC) is concrete containing fibrous material which increases its structural integrity. It contains short discrete fibres that are uniformly distributed and randomly oriented. Fibres include steel fibres, glass fibres, synthetic fibres and natural fibres. Within these different fibres that character of fibre reinforced concrete changes with varying concretes, fibre materials, geometries, distribution, orientation and densities.

The concept of using fibres as reinforcement is not new. Fibres have been used as reinforcement since ancient times. Historically, horsehair was used in mortar and straw in mud bricks. In the early 1900s, asbestos fibres were used in concrete, and in the 1950s the concept of composite materials came into being and fibre reinforced concrete was one of the topics of interest. There was a need to find a replacement for the asbestos used in concrete and other building materials once the health risks associated with the substance were discovered. By the 1960s, steel, glass (GFRC), and synthetic fibres such as polypropylene fibres were used in concrete, and research into new fibre reinforced concretes continues today.

## 2) Polymer Concrete

In the constructions industry new building materials with improved properties are required for satisfying the new utilization domains for modern construction or for repair works. The application of polymer on concrete has significantly progressed in the last 30 years. Polymers are either incorporated in a cement-aggregate mix or used as single binder. The composites made by using polymer along with cement and aggregates are called polymer-modified mortar or polymer-modified concrete, while composites made with polymer and aggregates are called polymer mortar or polymer concrete, depending on the maximum size of aggregate granule.

In the composition of polymer concrete there is not cement: the aggregates are bonded by the resin. Function of the type of polymer it can obtain concretes with synthetic resin, concretes with plastic resin or simple concrete with resin. The composite does not contain hydrated cement paste. Polymer concrete presents some advantages compared to the cement Portland concrete such as: rapid hardening, high mechanical strengths, improved resistance to chemical attack, durability, etc. One of the most important disadvantages is the high cost of resin that limited the use domains of polymer concrete. The performances of polymeric concrete depend on the polymer properties, type of filler and aggregates, curing temperature, components dosage, etc. The aggregates can be silicates, quartz, crushed stone, gravel, limestone, calcareous, granite, clay, etc. Near the aggregate, the filler is very important. Different types of fine materials can be used such as fly ash, silica fume, phosphor-gypsum, cinder, etc.

The different ingredients used for casting the concrete are as follows:

- a) **Waste Material:** Due to sustained pressure of industrial and developmental activities, there are appreciable disturbances in the ecological balance of nature. As with most large manufacturing industries, by-product materials are generated. These industrial by-product and waste materials must be managed responsibly to insure a clean and safe environment. The concept of environmental geo-techniques has emerged as an answer to the need to understand the ecological problems, connected with Fly ash, CKD, Quarry fines, Silica fines.
- **Fly ash:** Fly ash is one of the residues generated in combustion, and comprises the fine particles that rise with the gases. In an industrial context, fly ash usually refers to ash produced during combustion of coal. It is having a fineness of about 4000-8000  $\text{cm}^2/\text{g}$ . Fly ash is generally captured by electrostatic precipitators or other particle filtration equipment's before the flue gases reach the chimneys of coal-fired power plants. Depending upon the source and makeup of the coal being burned, the components of fly ash vary considerably. It may include one or more of the following elements or substances in quantities from trace amounts to several percents arsenic, beryllium, boron, cadmium, chromium, chromium VI, cobalt, lead, manganese, mercury, molybdenum, selenium, strontium, thallium, and vanadium, along with dioxins.
- **CKD:** Cement manufacturing is a critically important industry in the world worldwide production accounted for about 2.5 billion metric tons. Over the past several years dramatic advances have been achieved in the management and use of cement kiln dust, thus reducing its dependency on landfill disposal. Sustainability is the cornerstone of the cement industry, not only in the products that use cement, but also in its manufacturing process. Many of the older, inefficient plants are being replaced by more modern plants or being renovated with new technologies to be more efficient as well as more environmentally friendly. The majority of CKD is recycled back into the cement kiln as raw feed. In addition, new technology has allowed the use of previously land filled CKD to be used as raw feed stock. Recycling this by-product back into the kiln not only reduces the amount of CKD to be managed outside the kiln, it also reduces the need for limestone and other raw materials, which saves natural resources and helps conserve energy.
- **Quarry Fines:** In 2005, 216 million tonnes of saleable aggregate was produced; corresponding 55 million tonnes of quarry fines and 24 Million tonnes of quarry waste were also produced. The need to minimize fines production is driven by the Aggregates Levy (which has priced quarry fines out of the market in favour of recycled aggregate) and the Landfill Tax (which has made it expensive to dispose of fines). Future developments are likely to be driven by the need to respond to climate change. New crusher designs will be more automated, offer improved energy efficiency, have a greater production capacity and improved reliability.

- b) *Supplementary Cementing Materials (S.C.M.):* Supplementary cementing materials (SCMs) such as Meta-kaolin, Alccofine and GGBS are increasingly used in recent years as cement replacement material. They help to obtain both higher performance and economy. These materials increase the long term performance of the concrete through reduced permeability resulting in improved durability.
- *Meta-kaolin:* The necessity of high strength high performance concrete is increasing because of demands in the construction industry. Efforts for improving the characteristics of concrete over the past few years suggest that cement replacement materials along with chemical admixtures can improve the durability and corrosion characteristics of concrete. High Reactive Meta-kaolin (HRM), is a pozzolanic material that can be utilized to produce highly durable concrete composites. However, information to understand the behaviour of this mineral additive in concrete is insufficient. Some of the recent information is discussed in this paper highlighting the role of meta-kaolin in high strength high performance concrete.
  - *GGBS:* GGBS is non-metallic product consist of silicates and aluminates of calcium and other bases. The molten slag is rapidly chilled by quenching in water to form glassy sand like grains, further these grains ground to fineness less than  $45\mu$ . IS146:2000 suggest, GGBS obtained by grinding granulated blast furnace slag conforming to IS 12089 may be used as part replacement of OPC provided uniform blending with cement is ensured. When the GGBS is use as a replacement of cement the water requirement reduces to obtain the same slump. It also reduces the heat of hydration the main advantage of use of GGBS is reduction in permeability and increase resistance to chemical attack. Therefore GGBS is best applicable in the marine structure or concreting in the saline environment. This slag suitable for the use in combination with Portland cement in concrete, particular uses include concrete containing reactive aggregates, Large pours to reduce the risk of early-age thermal cracking, Concrete exposed to sulphates or aggressive ground & Concrete exposed to chlorides.
  - *Alccofine:* ALCCOFINE 1203 is a specially processed product based on slag of high glass content with high reactivity obtained through the process of controlled granulation. The raw materials are composed primary of low calcium silicates. The processing with other select ingredients results in controlled particle size distribution (PSD). The computed blain value based on PSD is around  $12000\text{cm}^2/\text{gm}$  and is truly ultrafine. Due to its unique chemistry and ultrafine particle size, ALCCOFINE1203 provides reduced water demand for a given workability, even up to 70% replacement level as per requirement of concrete performance. ALCCOFINE 1203 can also be used as a high range water reducer to improve compressive strength or as a super workability aid to improve flow.

## II. MATERIAL AND METHODOLOGY

### A. Materials

#### 1) Meta-kaoline

Meta Cem grades of Calcined clays are reactive aluminous silicate pozzolanformed by calcining very pure hydrous China clay. Chemically Meta Cem combines with Calcium Hydroxide to form Calcium Silicate and Calcium Alluminate Hydrates. Unlike other natural pozzolan MetaCem is water processed to remove uncreative impurities producing an almost 100 percent reactive material. The particle size of MetaCem is significantly smaller than cement particles. IS 456:2000 recommends use of Meta-kaolin as Mineral admixture.

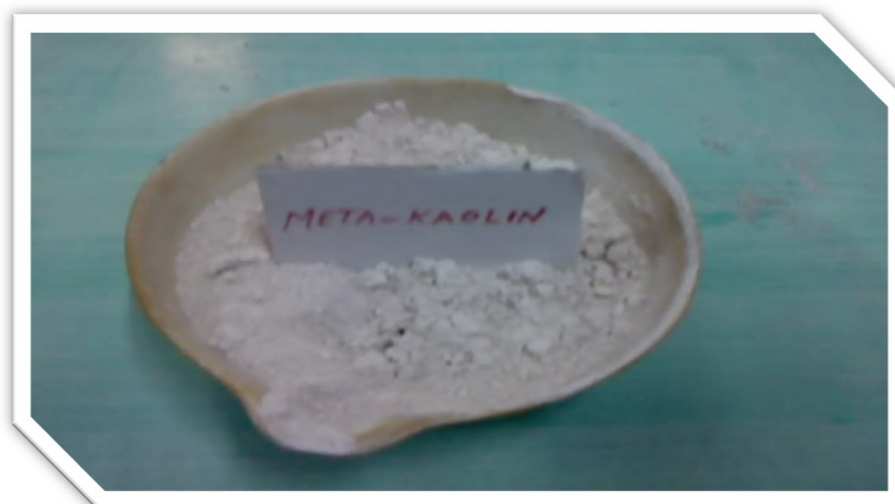


Fig No 1: Meta-kaolin

Table No 1: - Properties of Meta-kaolin

| PROPERTIES                                   | UNITS  | METACEM 85       | TEST METHOD  |
|--|--------|------------------|--------------|
| Physical Form                                | -      | Off white powder | -            |
| Specific Gravity                             | -      | 2.5              | ISO 787 / 10 |
| Bulk Density                                 | gm/ltr | 300 ± 30         | DIN 468      |
| Average Particle Size                        | μ      | 1.5              | Sedigraph    |
| Residue 325 #                                | %      | 0.5 max          | -            |
| Pozzolan Reactivity - mg Ca(OH) <sub>2</sub> | -      | >1000            | Chappel Test |

• *Benefits*

MetaCem is a thermally structured, ultrafine Pozzolan which replace industrial by products such as Silica fume / Micro silica. Commercial use of Meta-kaolin has already begun in several countries worldwide. Blending with Portland Cement MetaCem improves the properties of Concrete and Cement products considerably by:

- ✓ Increasing Compressive & Flexural Strength
- ✓ Providing resistance to chemical attack
- ✓ Reducing permeability substantially
- ✓ Preventing Alkali-Silica Reaction
- ✓ Reducing efflorescence & Shrinkage

• *Chemical Composition - WT*

SiO<sub>2</sub>+ Al<sub>2</sub>O<sub>3</sub> + Fe<sub>2</sub>O<sub>3</sub> > 96 %  
 Loss on Ignition < 1%

2) *GGBS*

Ground Granulated Blast Furnace Slag (GGBS): GGBS is obtained by quenching molten iron slag (a by-product of iron and steel making) from a blast furnace in water or steam, to produce a glassy, granular product that is then dried and ground into a fine powder. GGBS is used to make durable concrete structures in combination with ordinary port land cement and/or other pozzolanic materials. GGBS has been widely used in Europe, and increasingly in the United States and in Asia (particularly in Japan and Singapore) for its superiority in concrete durability, extending the lifespan of buildings from fifty years to a hundred years. Use of GGBS significantly reduces the risk of damages caused by alkali-silica reaction, higher resistance to chloride, and provides higher resistance to attacks by sulphate and other chemicals. GGBS is procured from visage steel plant (VSP).



Fig No.2: GGBS

The fineness modulus of GGBS using Blaine’s fineness is 320 m<sup>2</sup>/kg and other properties of GGBS given in table as below

Table No 2:- PROPERTIES OF GGBS

| Chemical Properties            | GGBS (%) |
|--------------------------------|----------|
| SiO <sub>2</sub>               | 34.06    |
| Al <sub>2</sub> O <sub>3</sub> | 18.8     |
| Fe <sub>2</sub> O <sub>3</sub> | 0.7      |
| CaO3                           | 2.4      |
| SO <sub>3</sub>                | 0.45     |
| MgO                            | 10.75    |
| S                              | 0.65     |
| MnO                            | 0.49     |
| Na <sub>2</sub> O              | 0.31     |
| K <sub>2</sub> O               | 0.98     |
| Cl                             | 0.008    |

• *Physical Properties*

|                          |  |
|--------------------------|--|
| Mean particle size       | 5 - 30 micron  |
| Colour                   | Off-white  |
| Odour                    | Odourless when dry but may give rise to sulphide odour |
| when wet                 |  |
| pH                       | When wet, up to 12                                     |
| Viscosity                | N/A  |
| Freezing point           | N/A  |
| Boiling point            | >1700°C  |
| Melting point            | >1200°C  |
| Flash point              | N/A (not flammable)                                    |
| Explosive properties     | N/A  |
| Density at 20°C          | 2.4 - 2.8 g/cm <sup>3</sup>                            |
| Water solubility at 20°C | <1g/l  |

Typically the strength development will be as shown in the following table:

Table No 3:- Strength achieved as percentage of 28-day strength

| Age     | 0% GGBS     | 50% GGBS    | 70% GGBS    |
|---------|-------------|-------------|-------------|
| 7-days  | 75%         | 45 to 55%   | 40 to 50%   |
| 28-days | 100%        | 100%        | 100%        |
| 90-days | 105 to 110% | 110 to 120% | 115 to 130% |

- Source Of Material:

Navdeep Construction Company RMC plant at Bhandup, Mumbai.

### 3) Alccofine

Alccofine is nothing but ultrafine slag. Alccofine performs in superior manner than all other minerals admixtures. Due to high CaO content, alccofine 1203 triggers two way reactions during hydration pozzolanic and hydraulic the result is denser pore structure and higher strength gain

- Classifications of Alccofine

Alccofine 1100 series – High calcium silicate products (cement base)

Alccofine 1200 series – Low calcium silicate products (slag base)

Alccofine 1300 series – Alumino silicate products (fly-ash based)



Fig No.3: Alccofine

- Optimum Particle Size Distribution

Use of alccofine 1203 enhance the performance of concrete in terms of durability due to its superior particle size distribution Alccofine 1203 has particles range 0.1 to 17 microns means average particle size is 4 microns

Table No 4: Physical Properties:

| Fineness (cm <sup>2</sup> /gm.) | Sp. Gravity | Bulk density (kg/m <sup>3</sup> ) | Particle distribution |                 |                 |
|---------------------------------|-------------|-----------------------------------|-----------------------|-----------------|-----------------|
|                                 |             |                                   | D <sub>10</sub>       | D <sub>30</sub> | D <sub>90</sub> |
| 8000                            | 3.1         | 700-900                           | 1.5                   | 5               | 9               |

Table No 5: Chemical Properties

| CaO   | SiO <sub>2</sub> | SO <sub>3</sub> | Al <sub>2</sub> O <sub>3</sub> | Fe <sub>2</sub> O <sub>3</sub> | MgO     | Cl        |
|-------|------------------|-----------------|--------------------------------|--------------------------------|---------|-----------|
| 61-64 | 21-23            | 2-2.4           | 5-5.6                          | 3.8-4.4                        | 0.8-1.4 | 0.03-0.05 |

Table No. 6: Setting Time

| Initial setting time | Final setting time |
|----------------------|--------------------|
| 60-120               | 120-150            |

- *Advantages*
- ✓ Durability is improved.
- ✓ Strength gain is improved.
- ✓ Improves the workability and cohesiveness.
- ✓ Better retention of workability.
- ✓ Reduces segregation.
- ✓ Lowers the heat of hydration.
- ✓ Improves the flow ability.
- ✓ Many decorating effects such as corrosion, carbonation and sulphate attack may be minimized or stopped.

Table No 7: Application

|                    |  |
|--------------------|--|
| SCM alccofine 1203 | High rise structure<br>Marine structure<br>Ports |
| Grouting alccofine | Tunnels<br>Dams<br>Bridges<br>Underground work's |

- Source of Material:  
Ambuja testing laboratory at J.B. Nagar Andheri, Mumbai.

*B. Methodology*

*1) Method of Mix Design*

Mix design procedure: As per I.S. 456 -2000

Concrete Mix Design: As per given Grade of Concrete.

- Material supplied:
- 1) Cement (P. P. C.)
  - 2) Sand
  - 3) Aggregate

Step: 1) Collection of data from laboratory.

- A) Cement sample tested as per I.S. 1489-1991 Part - I & test results are tabulated in Table- I.
- B) Sand: Physical properties are given in Table-II.
- C) Coarse aggregates: Physical properties are given in Table – III.

Step: 2) Decide target strength of mix design ( $f_t$ )

$$f_t = f_{ck} + t \cdot s$$

where,

- $f_t$  = Target comp. strength of concrete at 28 days.
- $f_{ck}$  = characteristic comp. strength of concrete at 28 days.
- t = statistical coefficient based on number results expected to be lower than the compressive strength.
- s =standard deviation based on degree of control.

Step: 3) Combining of all in aggregate 20mm nominal size by Graphical method.

Desired grading calculated from standard grading curve for 20mm aggregate curve.

As per the graph:

|           |       |       |       |         |          |         |       |       |       |
|-----------|-------|-------|-------|---------|----------|---------|-------|-------|-------|
| Sieve     | 40 mm | 20m m | 10m m | 4.75 mm | 2..36 mm | 1.18 mm | 600 μ | 300 μ | 150 μ |
| % passing |       |       |       |         |          |         |       |       |       |



Step: 4) Selection of W/C ratio, Water content & Air content.

For 20 mm graded aggregate:

- A) Water content: \_\_\_\_\_ Kg/m<sup>3</sup>
- B) Air content: \_\_\_\_\_ % by volume
- C) W/c ratio: \_\_\_\_\_

Step: 5) Adjustment of water content for change in condition.

| Change in condition           | Water content adjustment |
|-------------------------------|--------------------------|
| 1) For sand conform to Zone 1 | +1.5%                    |
| 2) For sand conform to Zone 2 | Nil                      |
| 3) For sand conform to Zone3  | -1.5%                    |
| 4) For sand conform to Zone 4 | -3%                      |
| For increase in Comp. Factor  |                          |
| 0.44                          | + 1.5 %                  |
| 0.45                          | + 1.5 %                  |
| 0.46                          | + 1.5 %                  |

Step : 6) Quantities of different ingredients:

| Particulars                                  | Mix-1                | Mix-2                | Mix-3                |
|--|----------------------|----------------------|----------------------|
| For W/c ratio                                | as per decided       | as per decided       | as per decided       |
| Total Volume considered (m <sup>3</sup> )    | 1.00                 | 1.00                 | 1.00                 |
| Volume of air (m <sup>3</sup> )              | From standard format | From standard format | From standard format |
| Volume of water (m <sup>3</sup> )            | From standard format | From standard format | From standard format |
| Weight of cement (kg) #                      | As per calculation   | As per calculation   | As per calculation   |
| Volume of cement (m <sup>3</sup> )           | As per calculation   | As per calculation   | As per calculation   |
| Volume of sand + aggregate (m <sup>3</sup> ) | As per calculation   | As per calculation   | As per calculation   |
| Volume of sand (m <sup>3</sup> )             | As per calculation   | As per calculation   | As per calculation   |
| Volume of 12 mm aggregate (m <sup>3</sup> )  | As per calculation   | As per calculation   | As per calculation   |
| Volume of 25 mm aggregate (m <sup>3</sup> )  | As per calculation   | As per calculation   | As per calculation   |
| Weight of sand (kg)                          | As per calculation   | As per calculation   | As per calculation   |
| Weight of 12 mm aggregate (kg)               | As per calculation   | As per calculation   | As per calculation   |
| Weight of 25 mm aggregate. (kg)              | As per calculation   | As per calculation   | As per calculation   |

Step: 7) Design proportion for one bag of cement in Kg.

| Mix   | Water | Cement | Sand | 12mm aggr. | 25mm aggr. | Total aggr. |
|-------|-------|--------|------|------------|------------|-------------|
| Mix-1 |       |        |      |            |            |             |
| Mix-2 |       |        |      |            |            |             |
| Mix-3 |       |        |      |            |            |             |

Step: 8) Actual quantities of materials to be added in one bag batch of concrete, Adjustment of water & sand due to absorption & free surface moisture.

| W/C ratio | Extra water for Absorption of C. A. in Kg | Reduced water for free surface moisture in Kg | Net quantity of water in Kg |
|-----------|---|---|-----------------------------|
|           |   |   |                             |
|           |   |   |                             |
|           |   |   |                             |

2) Actual proportions for one bag of cement, that to be actually added in Kg

| Mix with W/C ratio      |  |  |  |
|-------------------------|--|--|--|
| Cement (Kg)             |  |  |  |
| Water (Kg)              |  |  |  |
| Sand (Kg)               |  |  |  |
| Coarse aggr. 12 mm (Kg) |  |  |  |
| Coarse aggr. 25 mm (Kg) |  |  |  |

3) Procedure To Determine Workability Of Fresh Concrete By Slump Cone Test

- The internal surface of the mould is thoroughly cleaned and applied with a light coat of oil.
- The mould is placed on a smooth, horizontal, rigid and non-absorbent surface.
- The mould is then filled in four layers with freshly mixed concrete, each approximately to one-fourth of the height of the mould.
- Each layer is tamped 25 times by the rounded end of the tamping rod (strokes are distributed evenly over the cross section).
- After the top layer is rodded, the concrete is struck off the level with a trowel.
- The mould is removed from the concrete immediately by raising it slowly in the vertical direction.
- The difference in level between the height of the mould and that of the highest point of the subsided concrete is measured.
- This difference in height in mm is the slump of the concrete.

4) Procedure To Determine Workability Of Fresh Concrete By Compacting Factor Test

- The sample of concrete is placed in the upper hopper up to the brim.
- The trap-door is opened so that the concrete falls into the lower hopper.
- The trap-door of the lower hopper is opened and the concrete is allowed to fall into the cylinder.
- The excess concrete remaining above the top level of the cylinder is then cut off with the help of plane blades.
- The concrete in the cylinder is weighed. This is known as weight of partially compacted concrete.
- The cylinder is filled with a fresh sample of concrete and vibrated to obtain full compaction. The concrete in the cylinder is weighed again. This weight is known as the weight of fully compacted concrete.

| Workability | Compaction factor |
|-------------|-------------------|
| Very low    | 0.75-0.80         |
| Low         | 0.80-0.85         |
| Medium      | 0.85-0.92         |
| High        | Above 0.92        |

$$\text{Compacting factor} = \frac{\text{Weight of partially compacted concrete}}{\text{Weight of fully compacted concrete}}$$

### III. MIX DESIGN AND OBSERVATIONS

#### A. Method of Mix Design

Mix design procedure: As per I.S. 456 -2000

Target strength: M-30

Material supplied:

- 1) Cement (P. P. C.)
- 2) Sand
- 3) Aggregate

Step: 1) Collection of data from laboratory.

A) Sand: Physical properties like sieve analysis, water absorption, specific gravity.

B) Coarse aggregates: Physical properties like sieve analysis, water absorption, specific gravity.

Step: 2) Decide target strength of mix design ( $f_t$ )

$$f_t = f_{ck} + t \cdot s$$

Where,

$f_t$  = Target compressive strength of concrete at 28 days.

$f_{ck}$  = characteristic compressive strength of concrete at 28 days.

t = statistical coefficient based on number results expected to be lower than the compressive strength.

s = standard deviation based on degree of control.

$$f_t = f_{ck} + t \cdot s$$

$$f_t = 30 + (1.65 \times 6)$$

$$f_t = 39.9 \text{ N/mm}^2$$

Step: 3) Combining of all in aggregate 20mm nominal size by Graphical method.

Desired grading calculated from standard grading curve for 20mm aggregate curve

Table No 8 :-11% of different ingredient calculated from the graph

| 4.75& below | 4.75-10 | 10-20 | 20-40 |
|-------------|---------|-------|-------|
| 36%         | 12%     | 14.5% | 37.5% |
| 36%         | 26.5%   |       | 37.5% |

Step 4) Determination of Water Cement Ratio:

From graph for strength of 39.9 N/mm<sup>2</sup>

W.C. Ratio is = 0.375

= 0.40

= 0.42

Step 5) Determination of water content and sand content:

From IS code; For maximum size of agg. 25 mm:

Water Content is 180 Kg/m<sup>3</sup> and

For Sand = 33%

Step 6) Adjustment of water content for change in condition:

Desired grading (according to Zone B between standard curve 2<sup>nd</sup> and 3<sup>rd</sup>) from graph attached here with.

Table no: 9 water content for change in condition:

| Change in condition            | Water content adjustment |
|--------------------------------|--------------------------|
| 1) For sand conform to Zone II | Nil                      |

|                                      |         |
|--------------------------------------|---------|
| 2) For increase in Compaction Factor |         |
| 0.44                                 | + 1.5 % |
| 0.45                                 | + 1.5 % |
| 0.46                                 | + 1.5 % |

$$\text{Water content} = 180 + \frac{180 \times 1.5}{100}$$

$$= 182.7 \text{ kg/m}^3$$

Step 7) Cement content:

We have,

$$\text{W/C ratio} = 0.375$$

$$\text{Water} = 182.7 \text{ kg/m}^3$$

$$\text{Hence, Weight of cement} = \frac{182.7}{0.375}$$

$$= 487.2 \text{ kg}$$

Absolute volume of water and cement per cubic meter of concrete:

$$\text{Volume of water is } \frac{182.7 \text{ kg}}{1000} = 0.1827 \text{ m}^3$$

$$\text{Volume of cement is } \frac{487.2}{3.15} \times \frac{1}{1000} = 0.1546 \text{ m}^3$$

$$\text{Total volume} = 0.3373 \text{ m}^3$$

Step 8) Quantities' of aggregate:

$$\text{Total volume of aggregate} = (1.000 - 0.3373)$$

$$= 0.6627 \text{ m}^3$$

Absolute volume of sand (36%)

$$= 0.6584 \times 0.36$$

$$= 0.2386 \text{ m}^3$$

$$\text{Absolute volume of C.A.} = 0.6627 - 0.2386$$

$$= 0.4241 \text{ m}^3$$

$$\text{Weight of sand} = 0.2386 \times 2.63 \times 1000$$

$$= 627.52 \text{ kg.}$$

$$\text{Weight of coarse aggregate (12 mm)} = 0.1756 \times 2.91 \times 1000$$

$$= 510.99 \text{ kg.}$$

$$\text{Weight of coarse aggregate (25 mm)} = 0.2485 \times 2.94 \times 1000$$

$$= 723.14 \text{ kg.}$$

a) Table No. 10:- Mix proportion by weight:

| Water | Cement | Sand   | C.A 12mm | CA 25mm |
|-------|--------|--------|----------|---------|
| 182.7 | 487.2  | 627.52 | 510.99   | 723.14  |
| 0.375 | 1.0    | 1.179  | 0.743    | 1.808   |

b) Table No. 11:- Mix proportion by Volume:

| Cement | Sand   | C.A 12mm | CA 25mm |
|--------|--------|----------|---------|
| 0.3373 | 0.2386 | 0.1756   | 0.2485  |
| 1.0    | 0.6115 | 0.3484   | 0.8387  |

c) Table No. 12:-Quantity per bag of cement by weight:

| Water | Cement | Sand  | C.A 12mm | CA 25mm |
|-------|--------|-------|----------|---------|
| 0.375 | 1.0    | 1.179 | 0.743    | 1.808   |
| 18.75 | 50     | 58.95 | 37.15    | 90.4    |

**B. Correction for Water**

A) Extra water required for absorption in coarse aggregate 0.5%

$$127.55 \times \frac{0.5}{100} = 0.63 \text{ kg.}$$

B) Quantity of water to be deduction for free moisture present in sand at 1.5 %

$$58.95 \times \frac{1.5}{100} = 0.88 \text{ kg.}$$

Actual quantity of water to be added per bag of cement:

$$= 18.75 + 0.63 - 0.88$$

$$= 18.50 \text{ kg.}$$

C) Actual quantity of sand required to allow for mass of free moisture:

$$= 58.95 + 0.88$$

$$= 59.83 \text{ kg.}$$

Table No 13:- The quantities' per batch of one cement bag are:

| Water | Cement | Sand  | C.A 12mm | CA 25mm |
|-------|--------|-------|----------|---------|
| 18.75 | 50     | 59.83 | 37.15    | 90.4    |

Table No. 14:- Quantities of different ingredients:

| Particulars                                  | Mix-1  | Mix-2  | Mix-3  |
|--|--------|--------|--------|
| For W/c ratio                                | 0.375  | 0.40   | 0.42   |
| Total Volume considered (m <sup>3</sup> )    | 1.00   | 1.00   | 1.00   |
| Volume of air (m <sup>3</sup> )              | 0.20   | 0.20   | 0.20   |
| Volume of water (m <sup>3</sup> )            | 0.1827 | 0.1827 | 0.1827 |
| Weight of cement (kg) #                      | 487.2  | 456.75 | 435    |
| Volume of cement (m <sup>3</sup> )           | 0.1546 | 0.1450 | 0.1381 |
| Volume of sand + aggregate (m <sup>3</sup> ) | 0.6627 | 0.6723 | 0.6793 |
| Volume of sand (m <sup>3</sup> )             | 0.2386 | 0.2420 | 0.2445 |
| Volume of 12 mm aggregate (m <sup>3</sup> )  | 0.1756 | 0.1782 | 0.1800 |
| Volume of 25 mm aggregate (m <sup>3</sup> )  | 0.2485 | 0.2521 | 0.2547 |
| Weight of sand (kg)                          | 627.52 | 636.46 | 643.04 |
| Weight of 12 mm aggregate (kg)               | 510.99 | 518.56 | 523.80 |
| Weight of 25 mm aggregate. (kg)              | 723.14 | 733.61 | 741.18 |

Table no. 15:-Actual design proportion for one bag of cement in Kg:

| Mix   | Water   | Cement | Sand  | 12mm aggr. | 25mm aggr. | Total aggr. |
|-------|---------|--------|-------|------------|------------|-------------|
| Mix-1 | 18.50   | 50     | 64.40 | 52.50      | 74.20      | 259.60      |
| Mix-2 | 19.7340 | 50     | 69.68 | 56.77      | 80.34      | 276.524     |
| Mix-3 | 20.7125 | 50     | 73.91 | 60.23      | 85.17      | 290.023     |

Table No. 16:- Concrete Mix Design

| Trial mix | W/C ratio | Ingredient content in Kg |        |        |             |             | Mix proportion by weight |       |             |             | Compressive strength in Kg/cm <sup>2</sup> |                     |                     |                      |
|-----------|-----------|--------------------------|--------|--------|-------------|-------------|--------------------------|-------|-------------|-------------|--|---------------------|---------------------|----------------------|
|           |           | Water                    | Cement | Sand   | 12 mm aggr. | 25 mm aggr. | Cement                   | Sand  | 12 mm aggr. | 25 mm aggr. | 28 days field                              | 7 days lab required | 7 days lab observed | 28 days lab observed |
| M 1       | 0.375     | 182.7                    | 487.2  | 627.52 | 510.99      | 723.14      | 1.000                    | 1.288 | 1.05        | 1.484       | 300  | 266.14              | 294.85              | 413.85               |
| M 2       | 0.40      | 182.7                    | 456.75 | 636.46 | 518.56      | 733.61      | 1.000                    | 1.394 | 1.135       | 1.606       | 300  | 266.14              | 281.25              | 398.66               |
| M 3       | 0.42      | 182.7                    | 435.00 | 643.04 | 523.80      | 741.18      | 1.000                    | 1.478 | 1.205       | 1.703       | 300  | 266.14              | 275.33              | 393.25               |

Table No. 17:- Concrete Mix Design Recommended

| Trial mix | W/C ratio | Ingredient content in Kg |        |        |             |             | Mix proportion by weight |       |             |             | Compressive strength in Kg/cm <sup>2</sup> |                     |                     |                      |
|-----------|-----------|--------------------------|--------|--------|-------------|-------------|--------------------------|-------|-------------|-------------|--|---------------------|---------------------|----------------------|
|           |           | Water                    | Cement | Sand   | 12 mm aggr. | 25 mm aggr. | Cement                   | Sand  | 12 mm aggr. | 25 mm aggr. | 28 days field                              | 7 days lab required | 7 days lab observed | 28 days lab observed |
| M 2       | 0.40      | 182.7                    | 456.75 | 636.46 | 518.56      | 733.61      | 1.000                    | 1.394 | 1.135       | 1.606       | 300  | 266.14              | 281.25              | 398.66               |

Table No. 18:-Mix Proportion for 1kg of cement and cementitious material

| Mix   | Water | Cement | SCM  | Sand  | 12mm aggr. | 25mm aggr. |
|-------|-------|--------|------|-------|------------|------------|
| Mix-1 | 0.4   | 0.95   | 0.5  | 1.272 | 0.803      | 1.949      |
| Mix-2 | 0.4   | 0.9    | 0.10 | 1.272 | 0.803      | 1.949      |
| Mix-3 | 0.4   | 0.85   | 0.15 | 1.272 | 0.803      | 1.949      |
| Mix-4 | 0.4   | 0.8    | 0.20 | 1.272 | 0.803      | 1.949      |

Table No.19:- Quantity required per 60kg (Normal Concrete)

| Mix        | Water | Cement  | Sand    | 12mm aggr. | 25mm aggr. | Total Weight |
|------------|-------|---------|---------|------------|------------|--------------|
| Select Mix | 4.36  | 11.0389 | 15.3838 | 12.5340    | 17.7319    | 61.05        |

Table No. 20:- Quantity required per 60 kg (Alccofine Concrete)

| Mix         | Water | Cement  | Alccofine | Sand    | 12mm aggr. | 25mm aggr. | Total aggr. |
|-------------|-------|---------|-----------|---------|------------|------------|-------------|
| Mix-1(5%)   | 4.36  | 10.4869 | 0.5519    | 15.3838 | 12.5340    | 17.7319    | 61.05       |
| Mix-2(10%)  | 4.36  | 9.9350  | 1.1039    | 15.3838 | 12.5340    | 17.7319    | 61.05       |
| Mix-3 (15%) | 4.36  | 9.3831  | 1.6558    | 15.3838 | 12.5340    | 17.7319    | 61.05       |
| Mix-4(20%)  | 4.36  | 8.8311  | 2.2078    | 15.3838 | 12.5340    | 17.7319    | 61.05       |

Table No.21:-Quantity required per 60 kg (GGBS Concrete)

| Mix         | Water | Cement | GGBS   | Sand    | 12mm aggr. | 25mm aggr. | Total aggr. |
|-------------|-------|--------|--------|---------|------------|------------|-------------|
| Mix-1(5%)   | 4.36  | 9.9350 | 1.1039 | 15.3838 | 12.5340    | 17.7319    | 61.05       |
| Mix-2(10%)  | 4.36  | 9.9350 | 1.1039 | 15.3838 | 12.5340    | 17.7319    | 61.05       |
| Mix-3 (15%) | 4.36  | 9.3831 | 1.6558 | 15.3838 | 12.5340    | 17.7319    | 61.05       |
| Mix-4(20%)  | 4.36  | 8.8311 | 2.2078 | 15.3838 | 12.5340    | 17.7319    | 61.05       |

Table No 22:-Quantity required per 60 kg (Meta-kaoline Concrete)

| Mix         | Water | Cement | Meta-kaoline | Sand    | 12mm aggr. | 25mm aggr. | Total aggr. |
|-------------|-------|--------|--------------|---------|------------|------------|-------------|
| Mix-1(5%)   | 4.36  | 9.9350 | 1.1039       | 15.3838 | 12.5340    | 17.7319    | 61.05       |
| Mix-2(10%)  | 4.36  | 9.9350 | 1.1039       | 15.3838 | 12.5340    | 17.7319    | 61.05       |
| Mix-3 (15%) | 4.36  | 9.3831 | 1.6558       | 15.3838 | 12.5340    | 17.7319    | 61.05       |
| Mix-4(20%)  | 4.36  | 8.8311 | 2.2078       | 15.3838 | 12.5340    | 17.7319    | 61.05       |

C. Result of Slump cone test Carried out in Laboratory

All the tested concrete mixes gave the “Zero slump” as the mix is rich mix of M-30.

D. Results of Compaction Factor test Carried out in Laboratory

Table No: 23 Workability of Material

| Material used | Weight of partially compacted concrete(W <sub>1</sub> ) | Weight of fully compacted concrete(W <sub>2</sub> ) | Compacting factor | Workability |
|---------------|---|---|-------------------|-------------|
| Alkofine      | 19.110  | 22.610  | 0.72              | V. low      |
| GGBS          | 20.500  | 23.100  | 0.88              | Medium      |
| Metakoline    | 20.500  | 22.210  | 0.92              | Medium      |

E. Testing Reports of 28 Days

Table No. 24:- Normal concrete:

| CUBE SIZE          | CUBE NAME | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|--------------------|-----------|-----------|-------------------------------|--------|
| 15X15<br>(w/c=0.4) | 4         | 86100     | 382.66                        | 398.66 |
|                    | 5         | 90000     | 400.00                        |        |
|                    | 6         | 93000     | 413.33                        |        |

Table No. 25:- 5% Replacement of cement by Alccofine:

| CUBE SIZE | CUBE NAME      | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|-----------|----------------|-----------|-------------------------------|--------|
| 15X15     | A <sub>4</sub> | 87000     | 386.67                        | 400.00 |
|           | A <sub>5</sub> | 91000     | 404.44                        |        |
|           | A <sub>6</sub> | 92000     | 408.89                        |        |

Table No. 26:- 10% Replacement of cement by Alccofine:

| CUBE SIZE | CUBE NAME      | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|-----------|----------------|-----------|-------------------------------|--------|
| 15X15     | B <sub>4</sub> | 95625     | 425.00                        | 414.53 |
|           | B <sub>5</sub> | 96250     | 427.50                        |        |
|           | B <sub>6</sub> | 88000     | 391.11                        |        |

Table No. 27:- 15% Replacement of cement by Alccofine:

| CUBE SIZE | CUBE NAME      | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|-----------|----------------|-----------|-------------------------------|--------|
| 15X15     | C <sub>4</sub> | 69750     | 310.00                        | 383.70 |
|           | C <sub>5</sub> | 101250    | 450.00                        |        |
|           | C <sub>6</sub> | 88000     | 391.11                        |        |

Table No. 28:- 20% Replacement of cement by Alccofine:

| CUBE SIZE | CUBE NAME      | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|-----------|----------------|-----------|-------------------------------|--------|
| 15X15     | D <sub>4</sub> | 95100     | 422.50                        | 337.22 |
|           | D <sub>5</sub> | 72750     | 322.50                        |        |
|           | D <sub>6</sub> | 60000     | 266.67                        |        |

Table No. 29:- 5% Replacement of cement by GGBS:

| CUBE SIZE | CUBE NAME      | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|-----------|----------------|-----------|-------------------------------|--------|
| 15X15     | E <sub>4</sub> | 99000     | 440.00                        | 430.74 |
|           | E <sub>5</sub> | 99750     | 443.33                        |        |
|           | E <sub>6</sub> | 92000     | 408.89                        |        |

Table No. 30:- 10% Replacement of cement by GGBS:

| CUBE SIZE | CUBE NAME      | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|-----------|----------------|-----------|-------------------------------|--------|
| 15X15     | F <sub>4</sub> | 95000     | 422.22                        | 436.29 |
|           | F <sub>5</sub> | 100500    | 446.66                        |        |
|           | F <sub>6</sub> | 99000     | 440.00                        |        |



Table No. 31:- 15% Replacement of cement by GGBS:

| CUBE SIZE | CUBE NAME      | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|-----------|----------------|-----------|-------------------------------|--------|
| 15X15     | G <sub>4</sub> | 99000     | 440.00                        | 421.40 |
|           | G <sub>5</sub> | 99750     | 442.50                        |        |
|           | G <sub>6</sub> | 86000     | 382.22                        |        |

Table No. 32:- 20% Replacement of cement by GGBS:

| CUBE SIZE | CUBE NAME      | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|-----------|----------------|-----------|-------------------------------|--------|
| 15X15     | H <sub>4</sub> | 88500     | 392.50                        | 380.46 |
|           | H <sub>5</sub> | 90000     | 400.00                        |        |
|           | H <sub>6</sub> | 78500     | 348.89                        |        |

Table No. 33:- 5% Replacement of cement by Meta-Kaoline:

| CUBE SIZE | CUBE NAME      | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|-----------|----------------|-----------|-------------------------------|--------|
| 15X15     | C <sub>4</sub> | 99400     | 441.78                        | 439.11 |
|           | C <sub>5</sub> | 100000    | 444.45                        |        |
|           | C <sub>6</sub> | 97000     | 431.11                        |        |

Table No. 34:- 10% Replacement of cement by Meta-Kaoline:

| CUBE SIZE | CUBE NAME      | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|-----------|----------------|-----------|-------------------------------|--------|
| 15X15     | C <sub>4</sub> | 100700    | 447.55                        | 448.44 |
|           | C <sub>5</sub> | 102500    | 455.55                        |        |
|           | C <sub>6</sub> | 99500     | 442.22                        |        |

Table No. 35:- 15% Replacement of cement by Meta-Kaoline:

| CUBE SIZE | CUBE NAME      | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|-----------|----------------|-----------|-------------------------------|--------|
| 15X15     | C <sub>4</sub> | 68000     | 302.22                        | 383.70 |
|           | C <sub>5</sub> | 100000    | 444.44                        |        |
|           | C <sub>6</sub> | 94000     | 404.44                        |        |

Table No.-36:- 20% Replacement of cement by Meta-Kaoline:

| CUBE SIZE | CUBE NAME      | LOAD (Kg) | STRENGTH(Kg/cm <sup>2</sup> ) | AVG    |
|-----------|----------------|-----------|-------------------------------|--------|
| 15X15     | C <sub>4</sub> | 93000     | 412.50                        | 356.57 |
|           | C <sub>5</sub> | 98000     | 435.00                        |        |
|           | C <sub>6</sub> | 50000     | 222.22                        |        |

Table No.-37:-Test results of compressive strength of sample with Alccofine

| S.No. | QUANTITY OF MATERIAL (%) | 7 DAYS STRENGTH (Kg/cm <sup>2</sup> ) | 28 DAYS STRENGTH (Kg/cm <sup>2</sup> ) |
|-------|--------------------------|---------------------------------------|--|
| 1     | 0                        | 281.25                                | 398.66                                 |
| 2     | 5                        | 363.70                                | 400.00                                 |
| 3     | 10                       | 397.03                                | 414.53                                 |
| 4     | 15                       | 319.81                                | 383.70                                 |
| 5     | 20                       | 317.41                                | 337.22                                 |

Table No.- 38:-Test results of compressive strength of sample with GGBS

| S.No. | QUANTITY OF MATERIAL (%) | 7 DAYS STRENGTH (Kg/cm <sup>2</sup> ) | 28 DAYS STRENGTH (Kg/cm <sup>2</sup> ) |
|-------|--------------------------|---------------------------------------|--|
| 1     | 0                        | 281.25                                | 398.66                                 |
| 2     | 5                        | 290.52                                | 430.74                                 |
| 3     | 10                       | 299.62                                | 436.29                                 |
| 4     | 15                       | 250.74                                | 421.40                                 |
| 5     | 20                       | 227.77                                | 380.46                                 |


Table No.-39:-Test results of compressive strength of sample with Meta-kaoline

| S. No. | QUANTITY OF MATERIAL (%) | 7 DAYS STRENGTH (Kg/cm <sup>2</sup> ) | 28 DAYS STRENGTH (Kg/cm <sup>2</sup> ) |
|--------|--------------------------|---------------------------------------|--|
| 1      | 0                        | 281.25                                | 398.66                                 |
| 2      | 5                        | 310.10                                | 439.11                                 |
| 3      | 10                       | 316.29                                | 448.44                                 |
| 4      | 15                       | 307.33                                | 383.70                                 |
| 5      | 20                       | 259.62                                | 356.57                                 |


#### IV. RESULTS AND DISCUSSION

##### A. Results


Graph 1: for test result of compressive strength of sample with Alccofine

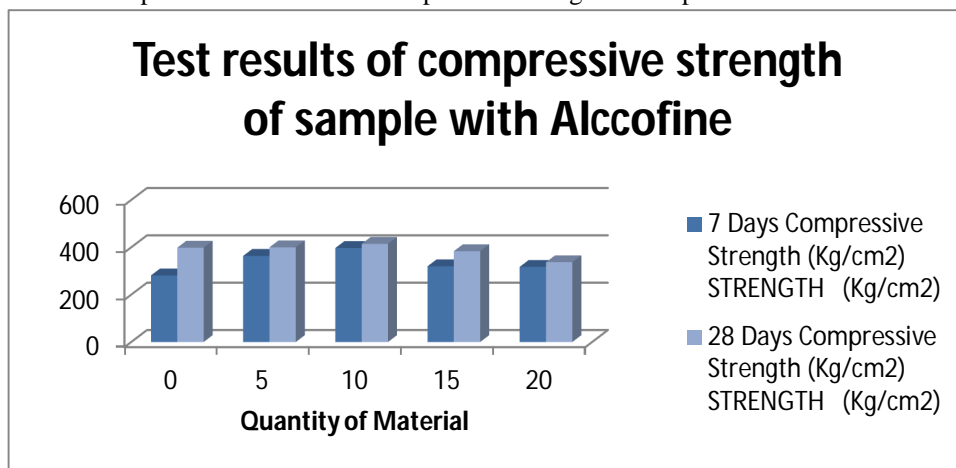

Graph 2: for test result of compressive strength of sample with GGBS

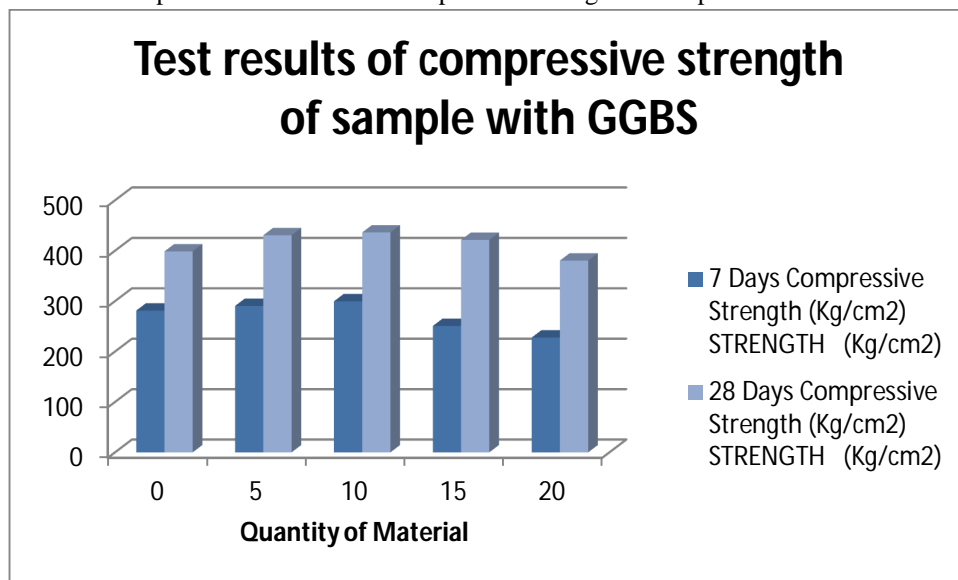

Graph 3: for test result of compressive strength of sample with Meta-Kaoline

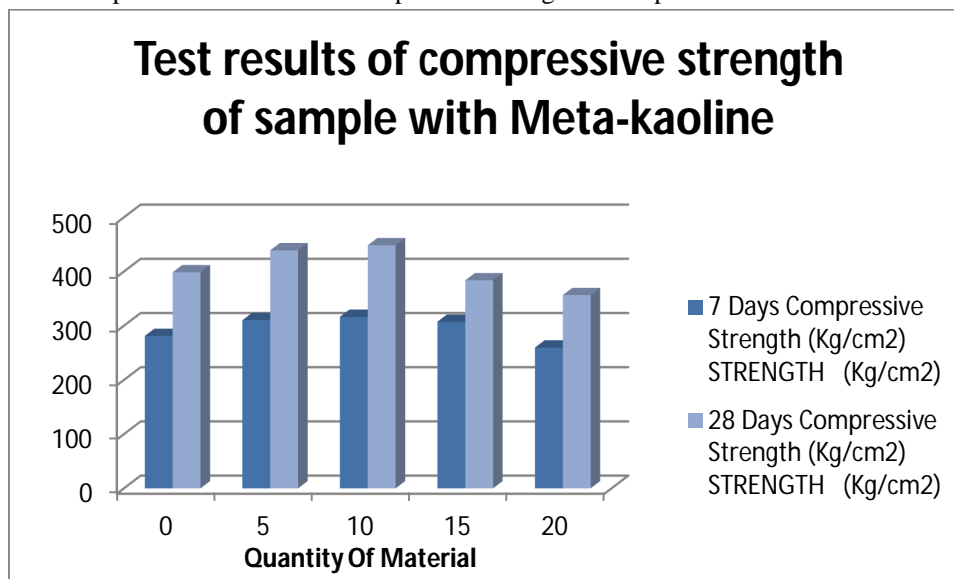

### V. CONCLUSION & RECOMMENDATION FOR FUTURE WORK

By conducting the study of 5%, 10%, 15% and 20% replacement of cement by different wastes and tested for workability and compressive strength we conclude that,

- 1) Using alccofine as a replacing material we get full design strength and workability for 5% and 10% of replacement.
- 2) Using GGBS as a replacing material we get full design strength and workability for 5%, 10% and 15% of replacement.
- 3) Using meta-kaoline as a replacing material we get full design strength and workability for 5%, 10% and 15% of replacement.

Thus we conclude that we can replace cement by:

- Alccofine 10%
- GGBS 15%
- Meta-kaoline 10%

Even for high strength mix such as M-30.

#### A. Recommendation For Future Work

Further research and investigation were highly recommended and should be carried out to understand more mechanical properties of prepared concrete. Some recommendation for future studies are mentioned below:

- 1) The effect of addition of fibre in our concrete mix can be checked by preparing the test samples with addition of different fibres.
- 2) More investigations and laboratory tests should be done to study on the mechanical properties of our concrete mix. Such application of prepared concrete was recommended in testing on concrete slabs, beam and walls or conducting more tests such as abrasion, shatter, shear, impact, blasting or creeping of concrete.
- 3) The addition of various different admixtures in variable % can be checked.
- 4) The addition of other supplementary cementitious material like Rice Husk ash, Sugar Cane ash, Fly ash and their combination in concrete mix can also be checked for compressive strength, Flexural strength and Split tensile strength.

#### REFERENCES

- [1] Alok Kumar et al(2016)- SSRG International Journal of Civil Engineering (SSRG-IJCE) – volume 3 Issue 5 – May 2016. <http://www.internationaljournalssrg.org>
- [2] Ansari U.S, Chaudhri I.M, Ghuge N.P, Phatangre R.R. “High Performance Concrete. with Partial Replacement of Cement by ALCCOFINE & Fly Ash”
- [3] M.S. Pawar- The International Journal Of Engineering And Science (IJES) ||Volume||2 ||Issue|| 6 ||Pages|| 05-09||2013|| ISSN(e): 2319 – 1813 ISSN(p): 2319 – 1805 [www.theijes.com](http://www.theijes.com) The IJES Page 5 Effect of Alccofine on Self Com
- [4] Saurabh Gupta et al A Review on Alccofine : A supplementary cementitious material (IJMTER) Volume 02, Issue 08, [August– 2015] ISSN (Online):2349–9745 ; ISSN (Print):2393-8161
- [5] Abhijitsinh Parmar, Dhaval M Patel “Experimental Study on High Performance Concrete by Using Alccofine and Fly Ash - Hard Concrete Properties”, International Journal of Engineering Research & Technology (IJERT) Vol. 2 Issue 12, December – 2013 ISSN: 2278-0181
- [6] Malvika Gautam, Dr. Hemant Sood Effect of Alccofine on strength characteristics of Concrete of different grades-A Review, International Research Journal of Engineering and Technology (IRJET) Volume: 04 Issue: 05 | May -2017 ISSN: 2395 -0056
- [7] M.Narmatha, Dr.T.Felixkala IOSR “Meta kaolin –The Best Material for Replacement of Cement in Concrete”, Journal of Mechanical and Civil Engineering (IOSR-JMCE) Volume 13, Issue 4 Ver. I (Jul. - Aug. 2016), e-ISSN: 2278-1684,p-ISSN: 2320-334X, PP 66-71 [www.iosrjournals.org](http://www.iosrjournals.org)
- [8] Aiswarya, Prince Arulraj, Dilip “A REVIEW ON USE OF METAKAOLIN IN CONCRETE”, IRACST – Engineering Science and Technology: An International Journal (ESTIJ), ISSN: 2250-3498, Vol.3, No.3, June 2013
- [9] Satyendra Dubey, Rajiv Chandak, R.K. Yadav “Effect of Metakaolin on Compressive Strength of Concrete”, Satyendra Dubey et al. Int. Journal of Engineering Research and Applications,ISSN : 2248-9622, Vol. 5, Issue 6, ( Part -4) June 2015, pp.80-82
- [10] CH Jyothi Nikhila and J D Chaitanya Kumar (2015) “Partial Replacement of Cement With Metakaolin in High Strength Concrete”, IJERST, ISSN 2319-5991 [www.ijerst.com](http://www.ijerst.com) Vol. 4, No. 4, November 2015



10.22214/IJRASET



45.98



IMPACT FACTOR:  
7.129



IMPACT FACTOR:  
7.429



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24\*7 Support on Whatsapp)