



# **iJRASET**

International Journal For Research in  
Applied Science and Engineering Technology



---

# **INTERNATIONAL JOURNAL FOR RESEARCH**

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

---

**Volume: 5      Issue: IX      Month of publication: September 2017**

**DOI:**

**[www.ijraset.com](http://www.ijraset.com)**

**Call:  08813907089**

**E-mail ID: [ijraset@gmail.com](mailto:ijraset@gmail.com)**

# Comparative Study of Ordinary Concrete and Eco Friendly Concrete

Yogesh. D. Nagvekar<sup>1</sup>, Vignesh. G. Ayyar<sup>2</sup>

<sup>1</sup>Asst. Professor, Civil Engineering Department, P.V.P.I.T., Bavdhan, Pune, India

<sup>2</sup>Student, Civil Engineering Department, MGM College of Engineering, Nanded, India.

**Abstract:** In today's modern world there has been enormous development in the field of "Concrete Technology". With this development there has also been enormous use of concrete in our day today life. Concrete mainly comprises of cement, sand and aggregate as its main constituents, which when mixed with water in correct proportion gives a byproduct called as "Concrete". The excess use of concrete has led to the environmental impact in terms of resources utilization as well as in terms of pollution. To overcome these impacts the concept of "Eco Friendly Concrete" came into existence. Eco Friendly Concrete is a concrete in which one or more of its constituents are replaced by a resource saving material, which ultimately has reduced environmental impacts in terms of both, resource utilization and pollution impacts together.

The current paper is an experimental work carried out to assess the comparative study of "Eco Friendly Concrete" and "Ordinary Concrete" in terms of their "Compressive Strength" parameter. M25 grade of Concrete was designed to carry out this experimental test. A comparative study of "Eco Friendly Concrete" with "Ordinary Concrete" was made based on the curing techniques. i.e. "Water Submerged Curing" and "Steam Curing".

**Keywords:** Eco Friendly Concrete, Ordinary Concrete, Compressive Strength, Water Submerged Curing, Steam Curing.

## I. INTRODUCTION

When we replace one or more constituents of Ordinary Concrete, by environmental friendly materials or recycled materials, the concrete formed is termed as "Eco Friendly Concrete". As we know the manufacturing process of cement and aggregate causes huge environmental impact, and day by day this increasing demand of concrete materials is ultimately causing impact to our environment. Thus replacing cement and aggregate (conventional constituents of concrete) can in turn help in minimizing the environmental impact caused during manufacturing process of aggregate and cement

The main objective of this research is to compare Ordinary Concrete and Eco Friendly Concrete in terms of compressive strength. To check the compressive strength property the "Ordinary Concrete" cubes were cured by "Water Submerged Curing" method, and the "Eco Friendly Concrete" cubes were cured by "Water Submerged Curing" method and another set by "Steam Curing" method. The curing of concrete cubes was carried out for 3 days, 7 days, and 28 days subsequently and cubes were tested respectively. The grade of concrete used use cast all the set of cubes was M25

## II. MATERIALS

### A. Cement

Ordinary Portland cement of 53 grade available in local market was used to prepare the cubes. The cement used was already tested for its various properties as per IS 4031-1988 and IS 12269-1987. Specific Gravity of cement was 3.09, while fineness was 2600 cm<sup>2</sup>/gram.

### B. Fine Aggregate

Locally available medium size crushed sand was used as fine aggregate. The fine aggregates confirmed to Zone-II of IS 383-1983. Specific Gravity of fine aggregate was 2.69 and Fineness Modulus of 3.23.

### C. Coarse Aggregate

Locally available crushed angular aggregates were used as coarse aggregates. The maximum size of coarse aggregate used was 20 mm. with Specific Gravity of 2.68 and Fineness Modulus of 7.2 for Ordinary Concrete. The maximum size of coarse aggregate for Eco Friendly Concrete was 20 mm and it was collected from the demolished construction sites.

### D. Fly Ash

Fly ash having grade C-618 was used.

**E. Alkaline Solution**

Sodium Hydroxide having molecular weight of 40gm was used. The sodium silicate (Na<sub>2</sub>SiO<sub>3</sub>) to sodium hydroxide solution (NaOH) ratio used in this experiment was 1.5

**F. Water**

The potable drinking water was used for the purpose of mixing concrete uniformly.

**III.MIX DESIGN**

Standard Mix Design for Ordinary Concrete was carried out as per IS standards Assuming the volume of overall aggregate as 65% and alkaline liquid to fly ash ratio as 0.30, the quantities of all ingredients used in conventional and Eco Friendly Concrete are mentioned below in TABLE I and TABLE II.

**TABLE I**  
MIXING PROPORTIONS OF ORDINARY CONCRETE

Sr. no	Constituents for M25	(Kg/m <sup>3</sup> )
1	Cement	320
2	Fine aggregate	751
3	Coarse aggregate	1356
4	Water	138
5	Water cement ratio	0.43

**TABLE III**  
MIXING PROPORTIONS OF ECO FRIENDLY CONCRETE

Sr. no	Ingredient for M25	(Kg/m <sup>3</sup> )
1	Fly ash	463.50
2	Fine aggregate	530.70
3	Coarse aggregate	1154.06
4	Sodium hydroxide solution	80
5	Sodium silicate solution	120

**IV. TEST PERFORMED ON THE AGGREGATE**

The various tests were performed on the aggregates included sieve analysis, flakiness and elongation index, specific gravity, impact value test and crushing of aggregates. All tests performed were confirmed to IS standards.

**V. MIXING AND CASTING OF CUBES**

The conventional method of mixing was used for geo-polymer concrete. At first of all ingredient were mixed in dry condition i.e. dry mix, for about 4-5 minutes. Then the combination of sodium hydroxide solution and sodium silicate solution was are added to the dry mix. The mixing was carried out in a trial mixer for about 6-8 minutes. The moulds were properly oiled and kept ready before pouring concrete into it.

After proper mixing of material, the concrete was poured into 150 mm X 150 mm X 150 mm size cube mould. For proper compaction of concrete was ensured by poured it in three layers and each layer was tamped 25 times. These cubes were demoulded after 24 hours. The cubes were then transferred for curing process.

**VI.CURING OF CUBES**

Water Submerged Curing” method was adopted for Ordinary Concrete cubes for 3days, 7days, and 28 days subsequently, and the cubes were submerged into a rectangular tank filled with water.

“Water Submerged Curing” method was also adopted for one set of Eco Friendly Concrete cubes. The another set of Eco Friendly Concrete was cured by “Steam Curing” method.

After demoulding, the cubes were placed in steam curing unit for 24 hours initially and then followed by water submerged curing

**VII. TEST RESULTS**

The results of compressive strength test conducted on both conventional and Eco Friendly Concrete after a span of 3 days, 7 days and 28 days are reflected in TABLE III, TABLE IV and TABLE V

**TABLE III**

**COMPRESSIVE STRENGTH TEST RESULTS OF ORDINARY CONCRETE**

Curing Days	Ordinary Concrete (Mpa)		
	3 Days	7 Days	28 Days
Average Strength of 3 Cubes Test	10.16	15.17	24.91

**TABLE IV**

**MIXING PROPORTIONS OF ECO FRIENDLY CONCRETE (WATER SUBMERGED CURING)**

Curing Days	Eco Friendly Concrete (Water Submerged Curing) (Mpa)		
	3 Days	7 Days	28 Days
Average Strength of 3 Cubes Test	4.82	8.56	13.19

**TABLE V**

**MIXING PROPORTIONS OF ECO FRIENDLY CONCRETE (STEAM CURING)**

Curing Days	Eco Friendly Concrete (Steam curing) (Mpa)		
	3 Days	7 Days	28 Days
Average Strength of 3 Cubes Test	15.86	22.92	27.77

Fig 1, Fig 2 and Fig 3 below reflects the comparison of compressive strength of Ordinary Concrete and Eco Friendly Concrete after 3 days, 7 days and 28 days subsequently.

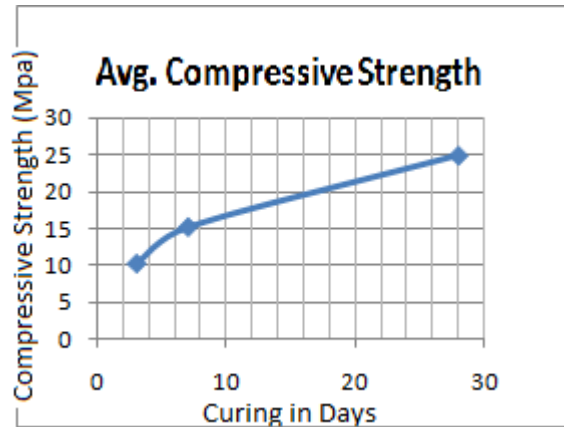


Fig. 1 Compressive Strength Test Results Of Ordinary Concrete

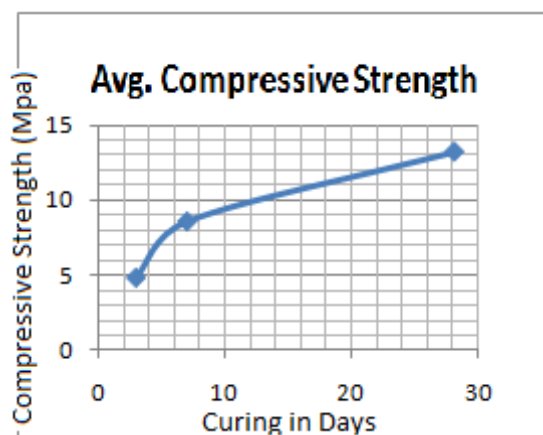


Fig. 2 Compressive Strength Test Results of Eco Friendly Concrete (Water Submerged Curing)

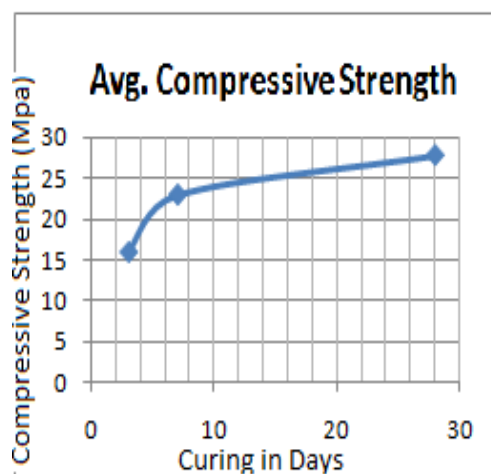


FIG. 3 COMPRESSIVE STRENGTH TEST RESULTS OF ECO FRIENDLY CONCRETE (STEAM CURING)

### VIII. CONCLUSIONS

The experimental result concludes that, the rate at which the compressive strength is gained by the Eco Friendly Concrete (under water submerged curing) is less compared to the compressive strength of the Ordinary Concrete (under water submerged curing). However, the compressive strength of the Eco Friendly Concrete (under steam curing) is very high compared to the other methods of cube curing carried out. It can be concluded that the strength gained by the Eco Friendly Concrete cubes under steam curing is 12% higher compared to the tests conducted on cubes in water submerged curing condition.



### REFERENCES

- [1] D.B. Desai, A.K. Gupta And Pradeep Kumar,(2013) "Eco Friendly Concrete: Need Of Environment", International Journal Of Advanced Science, Engineering And Technology, ISSN 2319-5924, Vol 2, Issue 2, pp. 134-137.
- [2] M.S. Kakamare, V.V. Nair, (February 2015) "Sustainable Construction Materials and Technology: Eco Friendly Concrete", International Journal of Advanced Technology In Engineering And Science. Volume No.03, Special Issue No. 02, ISSN: 2348 – 7550, Pp. 310-314.
- [3] M. Shahul Hameed And S. S. Sekar, (June 2009) "Properties Of Eco Friendly Concrete Containing Quarry Rock Dust And Marble Sludge Powder As Fine Aggregate", ARPJ Journal Of Engineering And Applied Sciences , ISSN 1819-6608 Vol. 4, No. 4, pp. 83-89.
- [4] Prof. Chetna. M. Vyas, Prof. (Dr.) Darshana R Bhatt, (July 2013) "Concept Of Eco Friendly Concrete Using Construction Demolished Waste As Recycled Coarse Aggregate", International Journal Of Engineering Trends And Technology (IJETT) – ISSN: 2231-5381, Volume 4, Issue 7, pp. 3160-3165.
- [5] Chirag Garg and Aakash Jain, (Feb 2014) "Eco Friendly Concrete: Efficient & Eco-Friendly Construction Materials", Impact: International Journal of Research In Engineering & Technology (Impact: IJRET), ISSN: 2321-8843, Vol. 2, Issue 2, pp. 259-264.
- [6] U.R.Kawade, P.A.Salunkhe, S.D.Kurhade, (April 2014) "Fly Ash Based Geopolymer Concrete", International Journal of Innovative Research In Science, Engineering And Technology, Volume 3, Special Issue 4, pp. 135-138.
- [7] Shivaji S. Bidwe and Ajay A. Hamane, "Effect of different molarities of sodium hydroxide solution on the strength of geopolymer concrete", American journal of engineering research, e-ISSN : 2320-0847, Volume 4, Issue 3, pp-139-145..
- [8] Swapnil Wanjari and Jerril Sebastian, (March 21, 2015) "Partial replacement of cement in geopolymer quarry rock dust concrete under different curing conditions", Proceedings of international conference on transportation and civil engineering, ISBN: 978-93-84468-19-4, pp 12-1



10.22214/IJRASET



45.98



IMPACT FACTOR:  
7.129



IMPACT FACTOR:  
7.429



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24\*7 Support on Whatsapp)