



iJRASET

International Journal For Research in
Applied Science and Engineering Technology



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Volume: 5 Issue: X Month of publication: October 2017

DOI: <http://doi.org/10.22214/ijraset.2017.10128>

www.ijraset.com

Call:  08813907089

E-mail ID: ijraset@gmail.com

Optimization of MIG Welding Parameters for Improving Strength of Welding Joint for Husquarna- Pulley of Material SAE-1018

¹Sudhir S. Kulkarni ²Rohan S. Jamgekar

^{1,2} P. G. Bharat-ratna Indira Gandhi College of Enng, Kegaon, Solapur, India,

Abstract: In this paper is used to study research work of Gas Metal Arc Welding(GMAW) show the effect of Current(A),Voltage(V),Gas Flow rate(L/Min) and Speed(M/Min) on Ultimate Tensile Strength(UTS) of SAE 1018 low alloy steel material, In this Experiment we done Experiment by using L9 orthogonal Array to find out UTS and also perform confirmatory Experiment to find out optimal run set of current, voltage speed and gas flow rate. Which is important to decide approach towards welding parameter validation? Effect of welding parameter also given in term of current, voltage, gas flow and wire feed. Also Taguchi method explains to optimization process. Root cause analysis done to know various factor and their effect on welding process

Index Terms: UTS, Weld Penetration, Taguchi Method, Welding Parameter Optimization, Root Cause Analysis, DMAIC.

I. INTRODUCTION

MIG welding is also recognized by gas metal arc welding. It is a semi-automatic process by which the arc length and feeding of wire into the arc can be controlled automatically and operator skills required to positioning the gun at a correct angle and moving it along the seam at a controlled travel speed in the metal transfer depends upon modular and spray transfer. The application of this process was for welding aluminum and As a result, the term MIG (Metal Inert Gas) welding was used and till now a days. Subsequent process developments included operation at low-current densities and pulsed direct current, application to a broader range of materials, and the use of reactive gases(particularly CO2) and gas mixtures.In this process consumable flux cored continuous wire or metallic electrode of diameter 0.8-2.4mm wound in spool form is fed at a required present speed through a welding gun, it picks up electric current from copper contact tube which is electrically connected to the DC power source and a shielding gases like argon, helium, carbon dioxide, carbon dioxide-argon mixture, argon-helium mixture. shielding gases are also use to cooled down the gun. MIG welding is use to increase productivity and consistency of quality.

II. PROBLEM IDENTIFICATION

Problem identification taken from industry by reviewing current process, rejection data, vender rating, customer satisfaction report and process owner comment about pain area. Here six sigma methodology was following to define exact problem. Generally according to six sigma DMAIC methodology to define problem and find appropriate solution.

Input Data received From Industry for Problem identification

Some data required to define problem and their exact root cause. Some quality tool can be used to arrange data and come on some conclusion. Seven Quality Control Tool can be to find out root cause of a problem. Here problem related welding was received from customer, nature of problem was shabby welding, blow hole, welding crack, spatter, un-fused wire, less penetration, fails in chisel test etc. rejection data collected from company. That data arrange as per below,

| Rejection at Customer End | | | | |
|---------------------------|--------------------------|----------|-------------|--------|
| Sr. No | Defect | Rej. Qty | cummulative | %cumml |
| 1 | Spatter | 82 | 82 | 32.16 |
| 2 | Shabby welding | 42 | 124 | 48.63 |
| 3 | Blow hole | 40 | 164 | 64.31 |
| 4 | Diameter over pin not ok | 31 | 195 | 76.47 |
| 5 | Un-fused welding wire | 14 | 209 | 81.96 |

| | | | | |
|-------|--------------------|-----|-----|--------|
| 6 | Under-cut | 12 | 221 | 86.67 |
| 7 | Diameter undersize | 12 | 233 | 91.37 |
| 8 | Keyway missing | 12 | 245 | 96.08 |
| 9 | Broken welding | 10 | 255 | 100.00 |
| Total | | 255 | | |

Table 1 Rejection at Customer End

| Inhouse Rejection Data | | | | |
|------------------------|--------------------------|----------------|------------|--------------|
| Sr.No. | Defect | Rejection qty. | Cumulative | % Cumulative |
| 1 | Spatter | 252.00 | 252.00 | 25.48 |
| 2 | Shabby welding | 210.00 | 462.00 | 46.71 |
| 3 | Blow hole | 148.00 | 610.00 | 61.68 |
| 4 | Diameter over pin not ok | 140.00 | 750.00 | 75.83 |
| 5 | Un-fused welding wire | 127.00 | 877.00 | 88.68 |
| 6 | Under-cut | 50.00 | 927.00 | 93.73 |
| 7 | Diameter undersize | 50.00 | 977.00 | 98.79 |
| 8 | Keyway missing | 12.00 | 989.00 | 100.00 |
| 9 | Broken welding | 0.00 | 989.00 | 100.00 |
| Total | | 989 | | |

Table 2 In-house Rejection Data

Pareto Chart For Customer Rejection

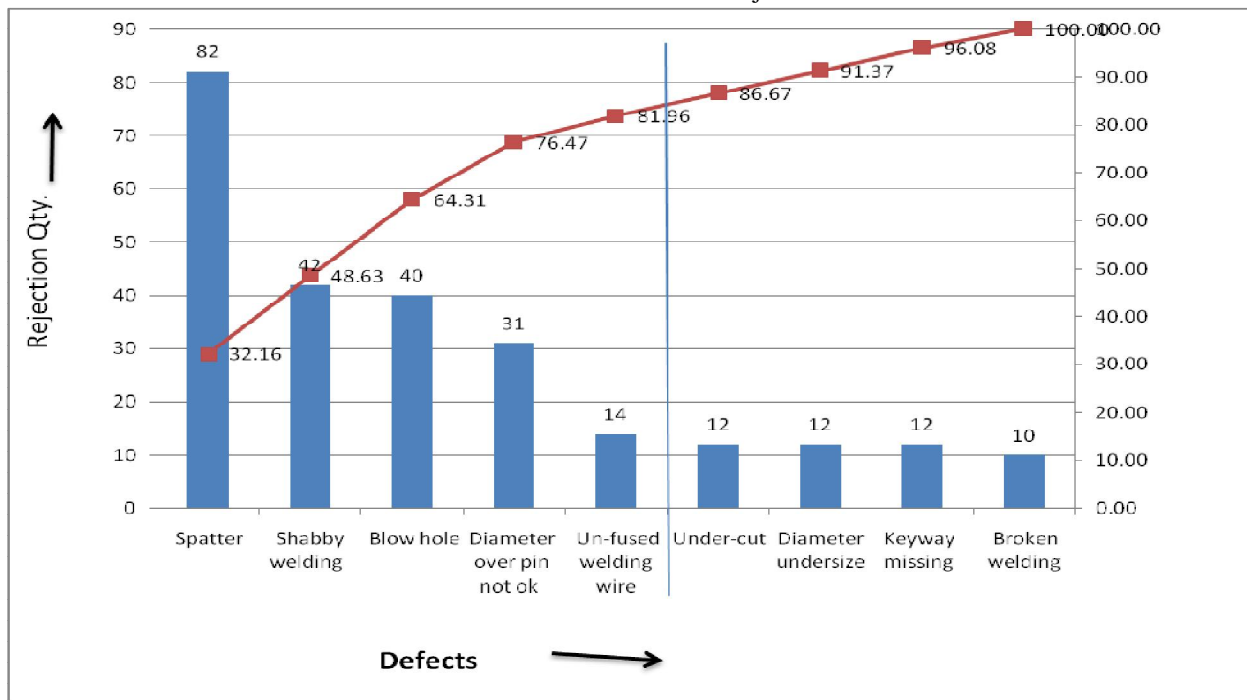


Fig.1. Pareto of rejection at Customer

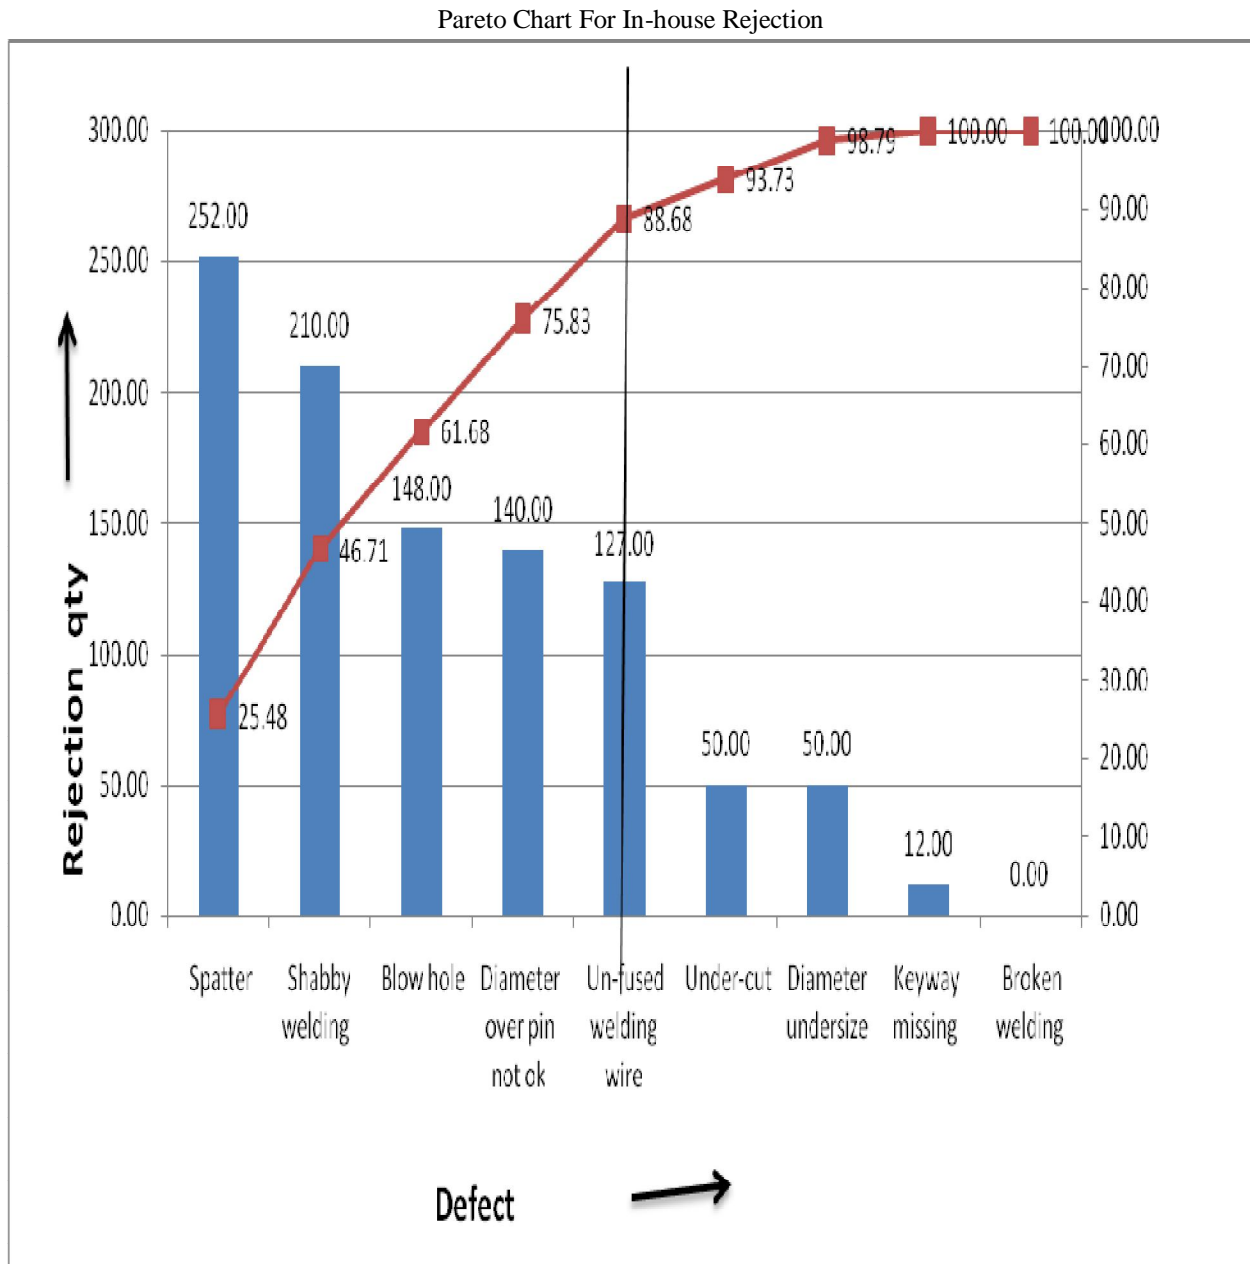


Fig.2 Pareto of rejection at In-house

From Pareto chart it is observed that most the defect contributing 80% of rejection from category of welding. Therefore the measure pain area is welding quality. Primary observation gives focus on welding quality and to define measure cause of defect depending on current process specification. It is need to verify existing system with control plan and thread to be find out. Some rejection noted of porosity found at welding section.

A. Root cause Analysis

For root cause analysis we are going to prepare cause and effect diagram. Generally we considering following parameters,

- 1) Man
- 2) Machine
- 3) Method
- 4) Environment

B. Cause and Effect Diagram

The major rate of defect is due to low skilled worker and no proper standards in production. Pareto Chart states that spatter, lack of fusion and crack are the three major defects. Process parameters play a vital role in eliminating the defects. From RCA, it is clearly visible that factors affecting defect rate.

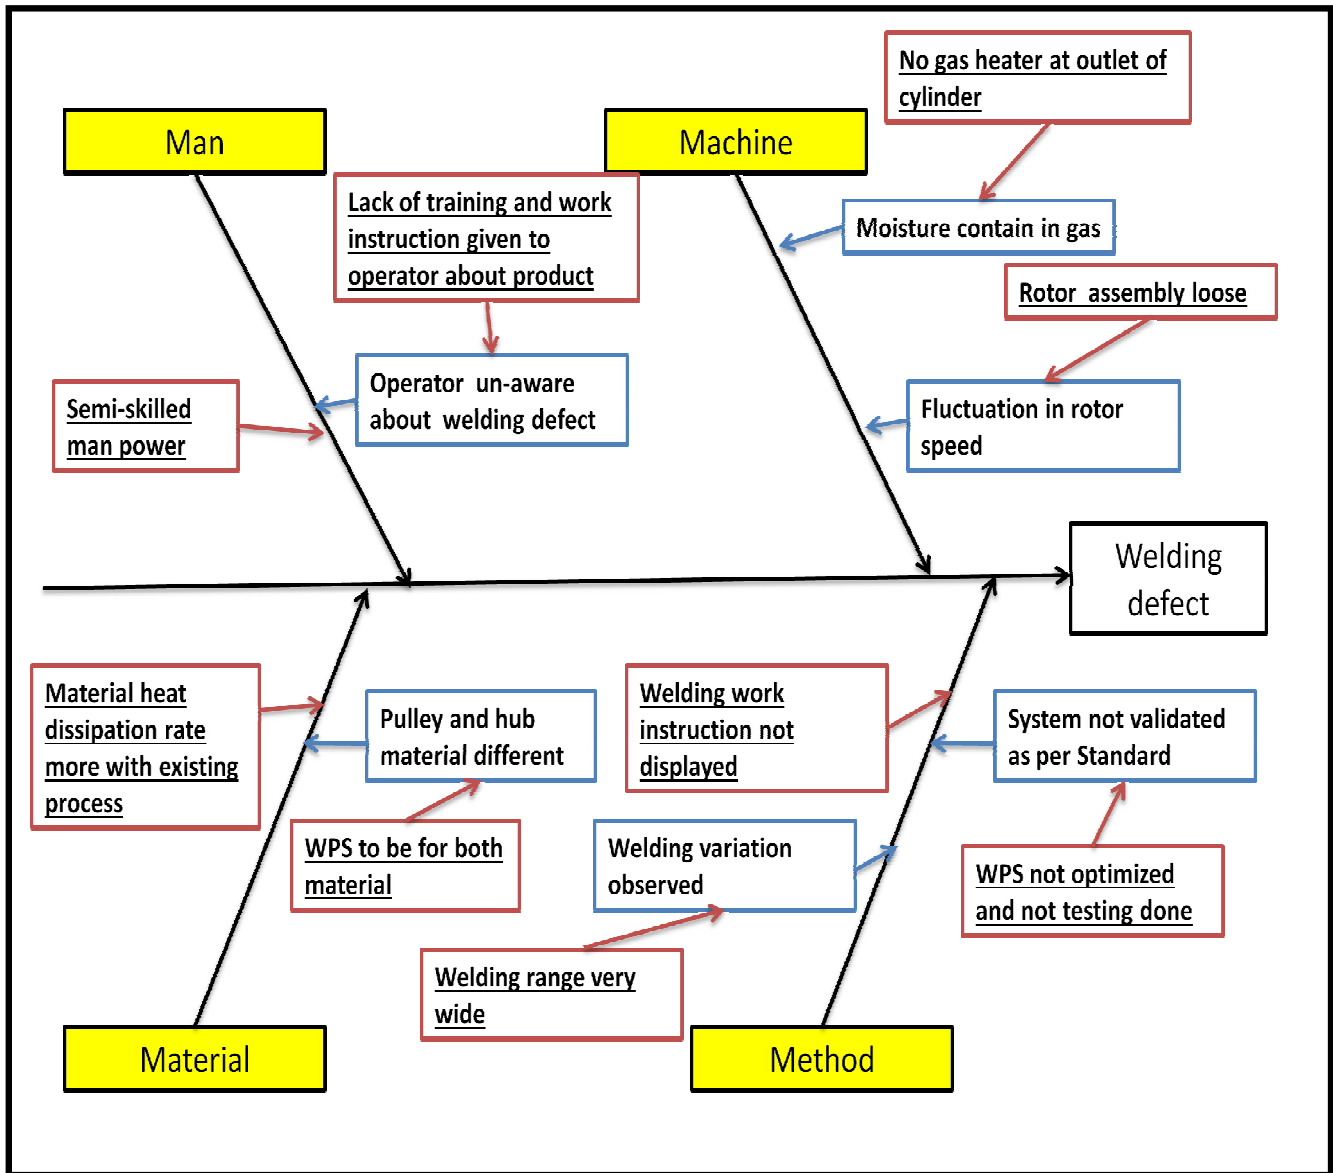


Fig 3. Ishikawa or Fishbone diagram

C. Root cause are as follows

- 1.No gas heater at outlet of cylinder.
2. Rotor assembly loose.
- 3.WPS not optimized and no testing done.
- 4.Welding work instruction not displayed.
5. Welding range wide.
6. WPS should such which match both material.
7. More heat dissipation.
8. Semi-skilled man power.
9. Lack of training material and aware to operator.

All root cause related with validation of welding process. Welding parameter should be studied and improve welding quality will tend to solve problem.

III. DESIGN OF EXPERIMENT USING TAGUCHI METHOD

Taguchi method used to optimize welding parameter on the basis of penetration and visual quality defect. Hence orthogonal array method used to solve problem. Here Taguchi method solved by using minitab-17 software which is gives good analytical result. And avoid so many equation calculation. Penetration test carried out in-house and final sample checked in lab.

A. Process variables and their values


| Factor | Affecting Factor | Level 1 | Level 2 | Level 3 | Level 4 |
|--------|---------------------|---------|---------|---------|---------|
| A | Wire feed (m/min) | 2.8-3.2 | 2.8-3.2 | 3.0-3.2 | 2.8-3.2 |
| B | current (A) | 100-140 | 100-120 | 100-120 | 100-140 |
| C | voltage (V) | 18-24 | 20-22 | 18-24 | 18-20 |
| D | Gas flow (Lit/min) | 10-12 | 10-15 | 10-12 | 10-15 |
| E | Machine speed (sec) | 20-30 | 25-27 | 25-30 | 20-25 |

B. Orthogonal array and Mean of Penetration

| A | B | C | D | E | Penetration | MEAN1 |
|---|---|---|---|---|-------------|-------|
| 1 | 1 | 1 | 1 | 1 | 0.68 | 0.68 |
| 1 | 2 | 2 | 2 | 2 | 0.95 | 0.95 |
| 1 | 3 | 3 | 3 | 3 | 0.97 | 0.97 |
| 1 | 4 | 4 | 4 | 4 | 0.84 | 0.84 |
| 2 | 1 | 2 | 3 | 4 | 0.82 | 0.82 |
| 2 | 2 | 1 | 4 | 3 | 0.94 | 0.94 |
| 2 | 3 | 4 | 1 | 2 | 1.06 | 1.06 |
| 2 | 4 | 3 | 2 | 1 | 0.84 | 0.84 |
| 3 | 1 | 3 | 4 | 2 | 0.72 | 0.72 |
| 3 | 2 | 4 | 3 | 1 | 0.73 | 0.73 |
| 3 | 3 | 1 | 2 | 4 | 0.74 | 0.74 |
| 3 | 4 | 2 | 1 | 3 | 0.82 | 0.82 |
| 4 | 1 | 4 | 2 | 3 | 0.72 | 0.72 |
| 4 | 2 | 3 | 1 | 4 | 0.6 | 0.6 |
| 4 | 3 | 2 | 4 | 1 | 0.64 | 0.64 |
| 4 | 4 | 1 | 3 | 2 | 0.7 | 0.7 |

Table 3 Orthogonal array and Mean of Penetration

C. Main effect plot for Mean

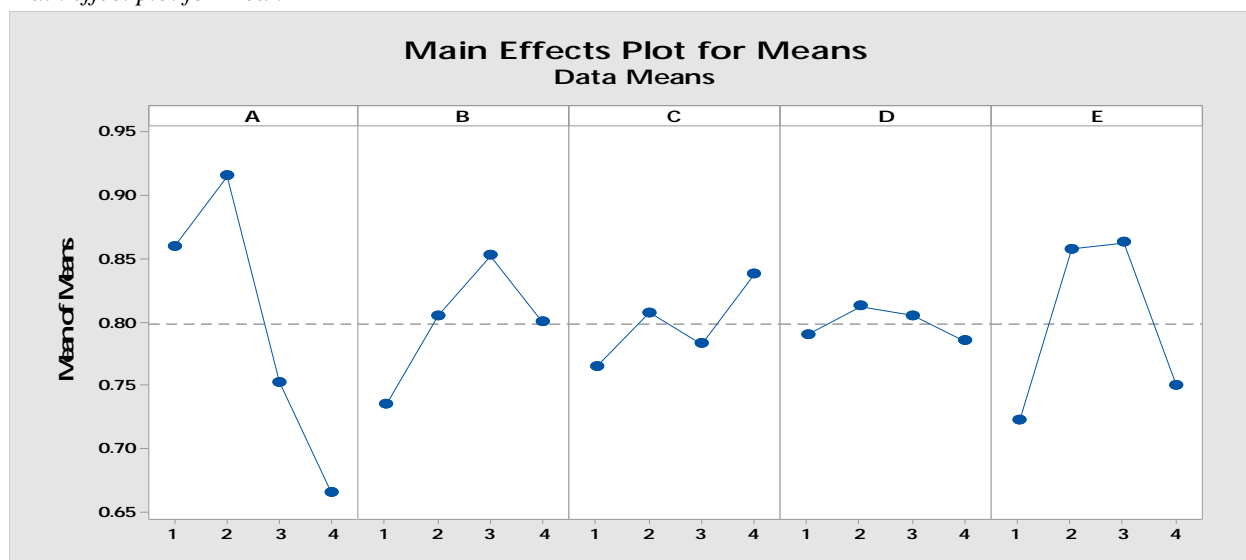

D. Factor Affected Level

Response Table for Means (Result obtain by Minitab)

| Level | A | B | C | D | E |
|-------|--------|--------|--------|--------|--------|
| 1 | 0.8600 | 0.7350 | 0.7650 | 0.7900 | 0.7225 |
| 2 | 0.9150 | 0.8050 | 0.8075 | 0.8125 | 0.8575 |
| 3 | 0.7525 | 0.8525 | 0.7825 | 0.8050 | 0.8625 |
| 4 | 0.6650 | 0.8000 | 0.8375 | 0.7850 | 0.7500 |
| Delta | 0.2500 | 0.1175 | 0.0725 | 0.0275 | 0.1400 |
| Rank | 1 | 3 | 4 | 5 | 2 |

E. Signal to Noise ratio (S/N Ratio)




Fig.4 Evaluation of problem in Minitab

F. Orthogonal Array with S/N Ratio

| | A | B | C | D | E | Penetration | MEAN1 | SNRA2 |
|---|---|---|---|---|---|-------------|-------|----------|
| 1 | 1 | 1 | 1 | 1 | 1 | 0.68 | 0.68 | -3.34982 |
| 1 | 1 | 2 | 2 | 2 | 2 | 0.95 | 0.95 | -0.44553 |
| 1 | 1 | 3 | 3 | 3 | 3 | 0.97 | 0.97 | -0.26457 |
| 1 | 1 | 4 | 4 | 4 | 4 | 0.84 | 0.84 | -1.51441 |
| 2 | 2 | 1 | 2 | 3 | 4 | 0.82 | 0.82 | -1.72372 |
| 2 | 2 | 2 | 1 | 4 | 3 | 0.94 | 0.94 | -0.53744 |
| 2 | 2 | 3 | 4 | 1 | 2 | 1.06 | 1.06 | 0.506117 |
| 2 | 2 | 4 | 3 | 2 | 1 | 0.84 | 0.84 | -1.51441 |
| 3 | 3 | 1 | 3 | 4 | 2 | 0.72 | 0.72 | -2.85335 |
| 3 | 3 | 2 | 4 | 3 | 1 | 0.73 | 0.73 | -2.73354 |
| 3 | 3 | 3 | 1 | 2 | 4 | 0.74 | 0.74 | -2.61537 |
| 3 | 3 | 4 | 2 | 1 | 3 | 0.82 | 0.82 | -1.72372 |
| 4 | 4 | 1 | 4 | 2 | 3 | 0.72 | 0.72 | -2.85335 |
| 4 | 4 | 2 | 3 | 1 | 4 | 0.60 | 0.60 | -4.43697 |
| 4 | 4 | 3 | 2 | 4 | 1 | 0.64 | 0.64 | -3.87640 |
| 4 | 4 | 4 | 1 | 3 | 2 | 0.70 | 0.70 | -3.09804 |

Table. 4 Orthogonal Array with S/N Ratio

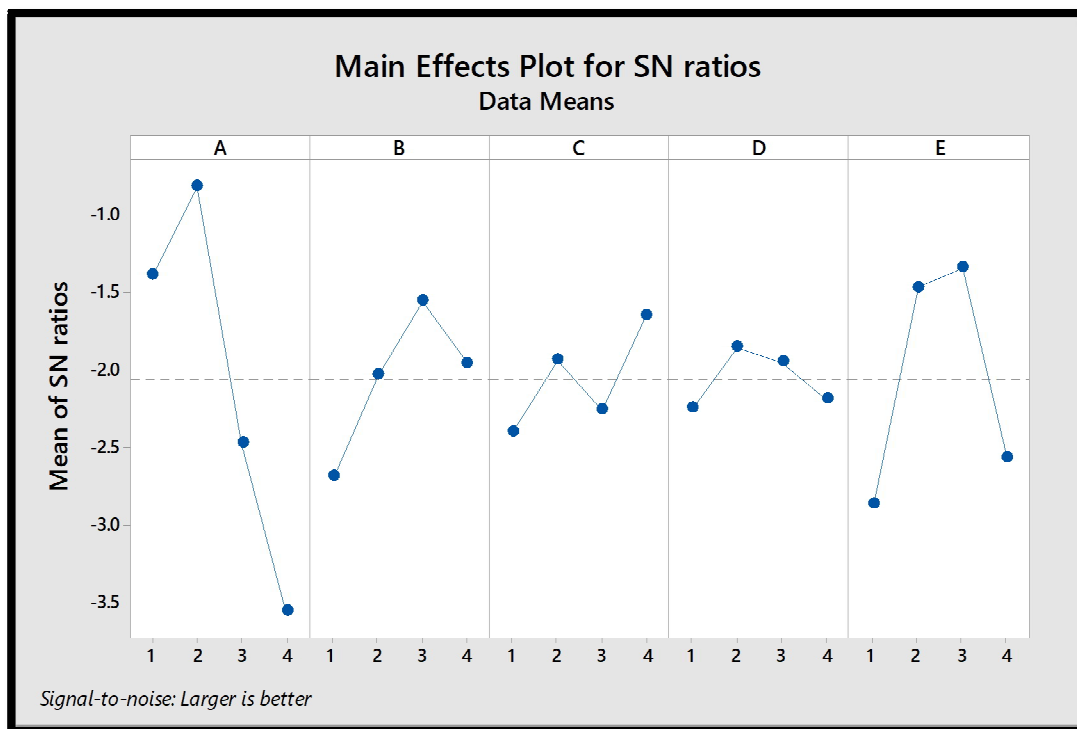


Fig. 5 Main effects plot for SN ratio.

| A | B | C | D | E | Penetration | MEAN1 | SNRA2 |
|----------|----------|----------|----------|----------|-------------|-------------|-----------------|
| 1 | 1 | 1 | 1 | 1 | 0.68 | 0.68 | -3.34982 |
| 1 | 2 | 2 | 2 | 2 | 0.95 | 0.95 | -0.44553 |
| 1 | 3 | 3 | 3 | 3 | 0.97 | 0.97 | -0.26457 |
| 1 | 4 | 4 | 4 | 4 | 0.84 | 0.84 | -1.51441 |
| 2 | 1 | 2 | 3 | 4 | 0.82 | 0.82 | -1.72372 |
| 2 | 2 | 1 | 4 | 3 | 0.94 | 0.94 | -0.53744 |
| 2 | 3 | 4 | 1 | 2 | 1.06 | 1.06 | 0.506117 |
| 2 | 4 | 3 | 2 | 1 | 0.84 | 0.84 | -1.51441 |
| 3 | 1 | 3 | 4 | 2 | 0.72 | 0.72 | -2.85335 |
| 3 | 2 | 4 | 3 | 1 | 0.73 | 0.73 | -2.73354 |
| 3 | 3 | 1 | 2 | 4 | 0.74 | 0.74 | -2.61537 |
| 3 | 4 | 2 | 1 | 3 | 0.82 | 0.82 | -1.72372 |
| 4 | 1 | 4 | 2 | 3 | 0.72 | 0.72 | -2.85335 |
| 4 | 2 | 3 | 1 | 4 | 0.6 | 0.6 | -4.43697 |
| 4 | 3 | 2 | 4 | 1 | 0.64 | 0.64 | -3.8764 |
| 4 | 4 | 1 | 3 | 2 | 0.7 | 0.7 | -3.09804 |

Table. 5 Orthogonal Array with S/N Ratio

Bold highlighted showing the large signal to noise ratio (S/N ratio). Means that the seventh experiment set gives us good penetration result. Also welding defect analyzed with these sample having good quality.

G. Result obtained for WPS

| Parameter | Level |
|--------------------------|---------|
| Wire feed (m/min) (A2) | 2.8-3.2 |
| current (A) (B3) | 100-120 |
| voltage (V) (C4) | 18-20 |
| Gas flow (Lit/min) (D1) | 10-12 |
| Machine speed (sec) (E2) | 25-27 |

Table 6 Result obtained for WPS

Trial conducted for above parameter and observed welding defects. One lot 1000 nos. taken for trial and result stated as flows. It is also called as production trial result.

| Rejection observed at Inhouse | | |
|-------------------------------|-----------------------|---------------------------------|
| 1 | Shabby welding | 1 |
| 2 | Broken welding | Taken 15 part no any failure |
| 3 | Spatter | 5 |
| 4 | Under-cut | 0 |
| 5 | Blow hole | 1 |
| 6 | Un-fused welding wire | 2 |
| 7 | Diameter undersize | 3 |

Table 7 Rejection observed at In-house

1 Result:-Here welding parameter are observed as follows

Current:- 100-120 A

Voltage:- 18-20 V

Gas flow:- 10-12 Ltr /Min

Wire feed:- 2.8-3.2 M/Min

Machine Speed:- 25-27 Sec

Penetration requirement :- As customer requirement is 20% throat size

$$h \geq 0.3 \text{ mm} + 0.1 a, \text{ but max. } 1 \text{ mm (both condition achieved)}$$

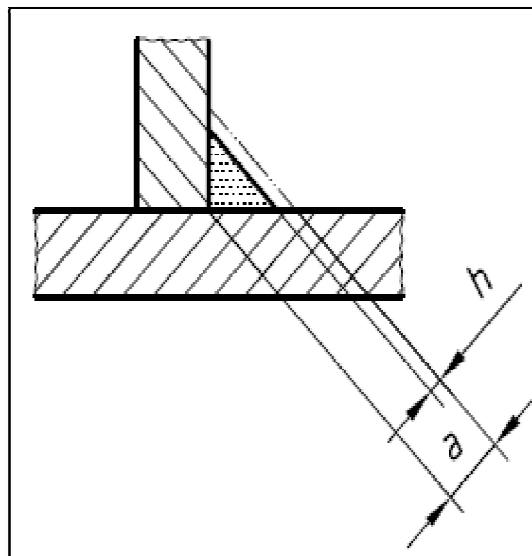


Fig. 6 Typical penetration schematics

IV. CONCLUSION

Taguchi optimization method was applied to find the optimal process parameters for penetration. A Taguchi orthogonal array, the signal-to-noise (S/N) ratio and analysis of variance were used for the optimization of welding parameters. A conformation experiment was also conducted and verified the effectiveness of the Taguchi optimization method. The improvement of S/N ratio is -3.34982. The experiment value that is observed from optimal welding parameters, the penetration is 1.06 mm. & S/N ratio is 0.506117.

REFERENCES

- [1] S.Utkarsh, P. Neel, Mayank T Mahajan, P.Jignesh, R. B.Prajapati:- have presented "Experimental Investigation of MIG Welding for ST-37 Using Design of Experiment" (International Journal of Scientific and Research Publications, Volume 4, Issue 5, May 2014 ISSN 2250-315)
- [2] Parametric optimization of MIG welding using Taguchi design method By S.V. sapakal, M.T. Telsang International Journal of Advanced Engineering Research and Studies E-ISSN2249-8974
- [3] Optimization of MIG welding process parameters to predict maximum yield strength in AISI 1040 by Ajit Hooda, Ashwani Dhingra and Satpal Sharma ISSN 2278 – 0149 Vol. 1, No. 3, October 2012
- [4] A Review on Optimization of MIG Welding Parameters using Taguchi's DOE Method by Satyaduttsinh P. Chavda, Jayesh V.Desai, Tushar M.Patel Volume-4, Issue-1, February-2014, ISSN No.: 2250-0758 International Journal of Engineering and Management Research
- [5] Metal Inert Gas (Mig) Welding Parameters Optimization By B. Mishra1, R.R. Panda and D. K. Mohanta International Journal of Multidisciplinary and Current Research ISSN: 2321-3124
- [6] Optimization of MIG welding for improves strength of welding joints International Journal of Advanced Engineering Research and Studies E-ISSN2249-8974 (Int. J. Adv. Engg. Res. Studies / II/ IV/July-Sept., 2013/14-16)
- [7] ISO 5817:2003 Welding — Fusion-welded joints in steel, nickel, titanium and their alloys (beam welding excluded) — Quality levels for imperfections
- [8] Optimization of Welding Parameter in MIG Welding by Taguchi Method-K. Sivasakthivel, K. Janarthanan, R. Rajkumar International Journal of Advanced Research in Mechanical Engineering & Technology (IJARMET) Vol. 1, Issue 1 (Apr. - Jun. 2015)
- [9] Effect of welding parameters in MMAW for joining of dissimilar metals and parameter optimization using artificial neural fuzzy interference system. U.S.Patil1, M.S.Kadam, International Journal of Mechanical Engineering and Technology (IJMET), ISSN 0976 – 6340(Print), ISSN 0976 – 6359(Online) Volume 4, Issue 2, March - April (2013) © IAEME
- [10] Welding Essentials by William L. Galverly Jr. and Frank B. Marlow, 2012
- [11] Welding Processing and technology by R. S. Parmar, Khanna Publisher, 2014
- [12] Welding Technology for Engineers by Baldev Raj, V Shankar, A K Bhaduri Narosa publication. 2015
- [13] Text Book of Welding Technology (PB) by Khanna O P, S.Chand Publication, 2014



10.22214/IJRASET



45.98



IMPACT FACTOR:
7.129



IMPACT FACTOR:
7.429



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24*7 Support on Whatsapp)