



# IJRASET

International Journal For Research in  
Applied Science and Engineering Technology



---

# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

---

**Volume: 6      Issue: 1      Month of publication: January 2018**

**DOI: <http://doi.org/10.22214/ijraset.2018.1197>**

**[www.ijraset.com](http://www.ijraset.com)**

**Call:  08813907089**

**E-mail ID: [ijraset@gmail.com](mailto:ijraset@gmail.com)**

# Experimental Investigation on Mechanical Properties of Jute/Glass Reinforced Hybrid Composite Laminate

Katla. Praveen Kumar<sup>1</sup>

<sup>1</sup>Assistant Professor Department of Mechanical Engineering St. Peter's Engineering College, Maisammaguda, Dhulapally, Medchal (Dist) TELANGANA STATE – 500100.

**Abstract:** *In the two last decades, extraction and use procedures of natural fibers have known an important increase for the reinforcement of composite materials called 'Bi-composites'. This category of fibers possesses a lot of advantages upon those traditional synthetic such as: Abundantly available, reduced cost, lightness and satisfactory specific performances. The current study has the aim of characterizing a new hybrid laminate made up of 4 plies; the upper and lower ones are reinforced with glass bidirectional fabrics while the two central ones are reinforced with natural Jute woven fabrics.*

*The main aim of this work is to get sufficient mechanical properties with reinforcing the most solicited layers with glass fabric and, in the same time, to ensure that an economy and a reduced weight through the reinforcement of the intermediate layers by Jute fabrics. The mechanical properties were carried out by two types of static trials: uniaxial tensile test, ILSS tests and 3-point bending in order to compare the mechanical properties of this laminate with those of a four layers with glass reinforced composite laminate. The mechanical trials have given us values of the hybrid laminate and properties were superior than those of the synthetically reinforced laminate in terms of Flexion and ILSS Strengths but lower in terms of tensile strength. And yet, performances obtained with hybrid Jute/ Glass reinforced laminates allow a prediction of actual perspectives for substituting glass fiber by others natural for semi- structural moderately loaded elements applications to combine performance and economy.*

**Keywords:** *Bio composites; Glass fibers; Mechanical characterization; Natural fibers*

## I. INTRODUCTION

The greatest challenge, nowadays, in all science fields is to face the rarefaction of fossil resources. The solution in civil engineering and in transportation is to lighten the construction materials. For this end, the composite materials have been, logically, imposed since the second half of the past century thanks to their specific mechanical characteristics [1]. These materials are emerging quickly as the potential substitute to the metal or ceramic based materials in number of applications including: automotive, aerospace, marine, sporting goods, electronic industries and for retrofitting the corrosion-damaged reinforced concrete elements [2,3]. These wonder materials with lightweight, high strength-to-weight ratio and stiffness properties have come a long way in replacing, technically and economically, the conventional materials like metals, wood etc. The replacement of steel with composites can save a 60-80 percentage of component weight and 20-50 weight percentages with the aluminium components [4]. Moreover, their cost has significantly decreased over the past years due to improvement of manufacturing [5]. The properties of polymers are modified using reinforcement fibers for optimizing the mechanical properties. Fabric, yarn and Fiber are some of the reinforcement forms that are usually applied to fiber reinforced composites. The most used fibers are: Carbon, aramid and glass ones. Fiber glass is a light weight, strong and robust material used due their excellent properties. Even though The strength characteristics are somewhat lower than carbon fiber and it is less stiff, the material is typically far less brittle and its raw materials are too much cheaper [6]. Non degradability, High cost of synthetic fibers and their health hazards have really necessitated the exploration of natural fibers; consequently, these latter have always formed wide applications from the time they gained commercial recognition [7]. Government regulations and a growing environmental consciousness throughout the world have generated a paradigm to move in the direction of designing materials compatible with the environment [8]. The early part of the 21 century gave more focus on renewable sources of natural fibers, mainly for composite materials applications in response to environmental issues [9] Natural fiber reinforced composites were introduced since 1908 when, for the first time, cellulose fibers were incorporated in phenolic resins [10]. The advantages of natural fibers include: abundant sources in the nature, renewability, biodegradability, non-toxicity, low cost, easy processing, low specific gravity, high toughness, acceptable specific strength, sustainable resource, good thermal properties and enhanced energy recovery [11-14]. Diversification of jute fibers from their traditional markets to other potential sectors (building

and furniture) has gained interest in developing countries to meet the pressing demands of conventional materials, especially wood substitutes. [15].

Previously, the natural fiber reinforced laminates have an interest in abundant applications: Non-structural parts of automotive industry [16], housing, railways and aerospace applications [17, 18]. The wide applications of NFPC's are growing rapidly in numerous engineering fields; a great importance in different automotive applications by many automotive companies (BMW, Mercedes, Chrysler, Ford and Opel). Beside the auto industry, the applications of natural fiber composites have also been found in building and construction industry, the application of natural fiber composites have also been found in building and construction industr, sports, aerospace, panels, windows frame, decking and bicycle frame [19]. Jute fiber is abundantly available all over the world [20]. One of the most promising applications of jute is in polymer composites that can be molded into a variety of flat and complex shaped components by exploiting their attractive reinforcing potential. The below graph and table gives a comparison between the mechanical properties of Jute and Glass fibers(Table 1).

The importance of interfacial interactions between the polymer matrix and the fillers was widely reported as to improve the hydrothermal stability and mechanical properties of polymer composites. This is why several techniques have been applied to remove incompatibility problems by using coupling agents and/or chemical surface fillers modification. Another way to improve the properties of composites is to use more than one type of reinforcement and produce hybrid composites. These materials are one of the most promising areas in polymer composites. By using a combination of inorganic and organic fillers (hybridization) in thermoplastics leads to the development of hybrid organic/inorganic polymer composites [21-23]. Many authors have reported the mechanical properties of natural fiber reinforced composites. But less effort has been focused on Natural-glass fiber reinforced polymers. So this paper provides overview of Natural-glass fiber reinforced polymers [24]. The main aim of this study is to preparation, properties and comparison of the properties of a Hybrid composite laminate reinforced with raw Jute/Glass fabrics with another Glass fiber reinforced laminate. Our targeted objectives through this research work are: Using renewable resources. Reduce Health problems and Skin irritations during manufacturing.

Fiber	Density(g/cm3)	Elongation (%)	Tensile strength(Mpa)	Youngs modulus(Gpa)	Specific modulus(Gpa)
Jute	1.2	2-3	400-750	13-24	7-16
E-glass	2.3	3.8	1800-3000	65-70	24-26

Table 1: Mechanical characteristics of jute and glass fibers [21, 22].

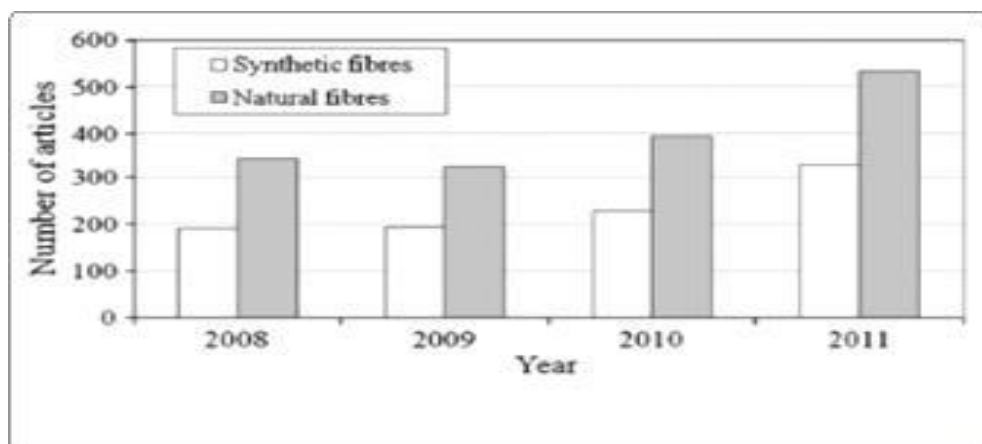


Figure 1: Number of published articles studying composites reinforced withsynthetic and natural fibers [18].

Trial Type	ASTM Standard
Tensile test	D3039
Three points bending	D790
ILSS	D2344

Table 2:Trials and their standards



Figure 2:Tensile test set-up.

Increase the cost/performance ratio. Protecting our environment and its resources.

## II. MATERIALS AND METHODS

### A. Materials

- 1) *Polymer binder:* The thermosetting unsaturated polyester resin is UPE resin has a density of 1.2 g/cm<sup>3</sup>, viscosity at 25° equals 426 mPas and a gel time at 25° equals 14'30''. The UPE resins are a commercially available polymer binder and are most frequently used thermosetting matrices owing to their low cost and adaptability to be transformed into large composite structures. Catalyst and accelerator in a weight ratio of 1:0.003:0.02
- 2) *Jute fibers:* Jute is a bast fiber obtained from inner tissues of the plant stem. The fibers are bound together by gummy materials (pectinous substances) which keep the fiber bundles cemented with non-fibrous tissues of Jute bark. The soft tissues can be softened, dissolved and washed away so that the fiber can be obtained from the stem. This is done by steeping the stems in water and it is known as retting. The optimum water temperature for retting is 80°F. Micro-organisms (mainly bacillus bacteria) decompose the gums and soften the tissues in 5 to 30 days depending upon temperature and the type of water used. It has been found that the presence of higher amounts of calcium and magnesium tend to increase the tenacity of fiber. We have used raw 'as received' jute fabrics without any further treatments. The approximate chemical composition of Jute fiber in wt% is: cellulose 71.5, hemicelluloses 13.4, pectin 0.2, lignin 13.1, water soluble compounds 1.2, fat and waxes 0.6. [25] (Figure 1).
- 3) *Fabrication method:* The composite laminates that were made in this study were fabricated by a simple hand lay-up technique. Each plate was constituted of 4 layers of reinforcement fabrics impregnated in pre-catalyzed binder. After manufacture, the composites stayed 24 hours to have a total polymerization [26]. The Glass/Jute hybrid and reinforced Glass composite laminates were characterized for mechanical characteristics on specimens cut with diamond saw from the manufactured polymer composite laminate plates according to ASTM standards as described in the Table 2 below:
- 4) *Mechanical Properties:* flexural, ILSS and Tensile test were conducted on a computerized Universal Testing machine UTM YLE 25 having a maximum capacity of 250 KN. All the tests were done at an ambient temperature.
- 5) *Tensile strength test:* The specimens of dimensions 250 mm × 25mm × 8mm were used for analysis. The tensile test was conducted in accordance with ASTM D3039 method (Figure 2). The test was conducted at the constant strain rate of 1.5 mm/min. Force was applied until the failure of the sample and load-elongation curve was obtained. The tensile modulus and strength were calculated through the formulas:

$$R_T = F_U/A \quad (1)$$

$$E_L = (F_1 - F_2) / \{(\epsilon_1 - \epsilon_2) \times A\} \quad (2)$$

$$\epsilon U = F_U / (E_L \times A) \quad (3)$$

where,  $F_U$ : ultimate load (N),  $F_1$  and  $\epsilon_1$ : The load and the strain at 50% of  $F_U$ ,  $F_2$  and  $\epsilon_2$ : The load and the strain at 20% of  $F_U$ .  $\epsilon U$ : the ultimate strain.

- 6) *Flexural strength test:* The Three-point bend flexural test was conducted in accordance with ASTM D790 Figure 3. The speed rate was 2 mm/min. Flexural strength is determined from the formula given below:

$$R = \frac{3FL}{2bd^2} \quad (4)$$

F

$$E_F = L^3 m / bd^3 \tag{5}$$

Where: F: Ultimate load (N), L: Span length (mm), b: wide (mm), d:

Thickness (mm), m: The slop of the curve load-bending in the linear zone.

- 7) *Inter-laminar shear strength test*: This test was carried out mainly to determine the delaminating effect of the plies and the inter-laminar shear strength (SH) of the composites according to ASTM D 2344. The specimens had span-to-length ratio of 3/7 and a thickness-to-span ration of 1/3 to avoid the flexural effects. The experimental set-up is illustrated on the Figure 3. (Figure 4)

The Inter-laminar shear Strength  $S_H$   
 $= 0.75 \times \text{Pd}$  MPa (6).  
Where Pd = breaking load, N.

### III. RESULTS AND DISCUSSION

#### A. Tensile strength test

Generally, the mechanical properties of obtained composites are



Figure 3: Flexural strength set-up.



Figure 4: ILSS set-up.

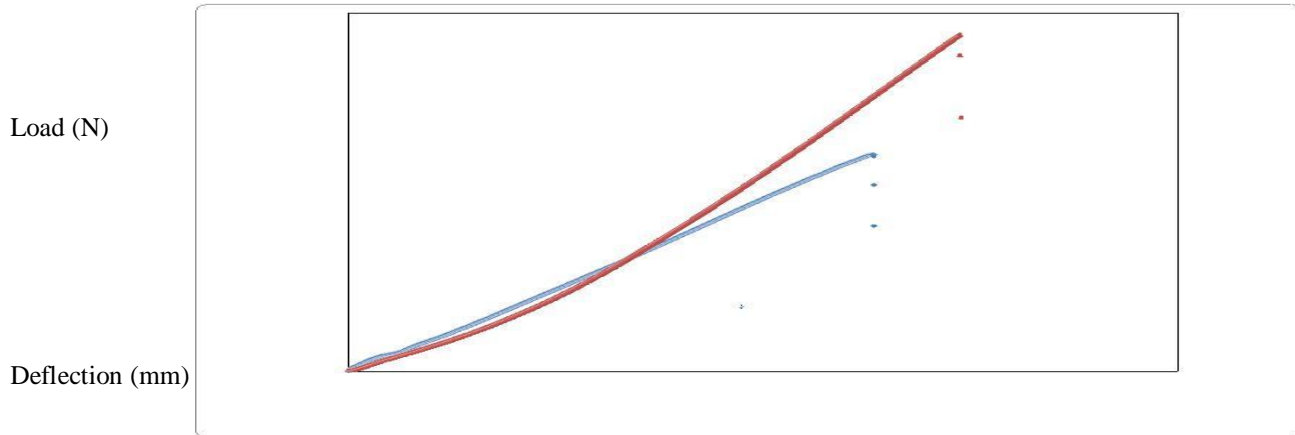


Figure 6: Load-deflection curve of the 3 laminates.

Hybrid Jute/woven Glass Laminate Woven Glass reinforced Laminate

Reinforcement type	Tensile Load (N)	Tensile Modulus(Gpa)	Elongation at break
Jute Fabric	8025.5 ± 1109	4.38 ± 0.56	6.25 ± 0.83
2D E-Glass Fabric	14645 ± 612	25.4 ± 1.67	9.13 ± 0.72

Table 3: Tensile properties of specimens.

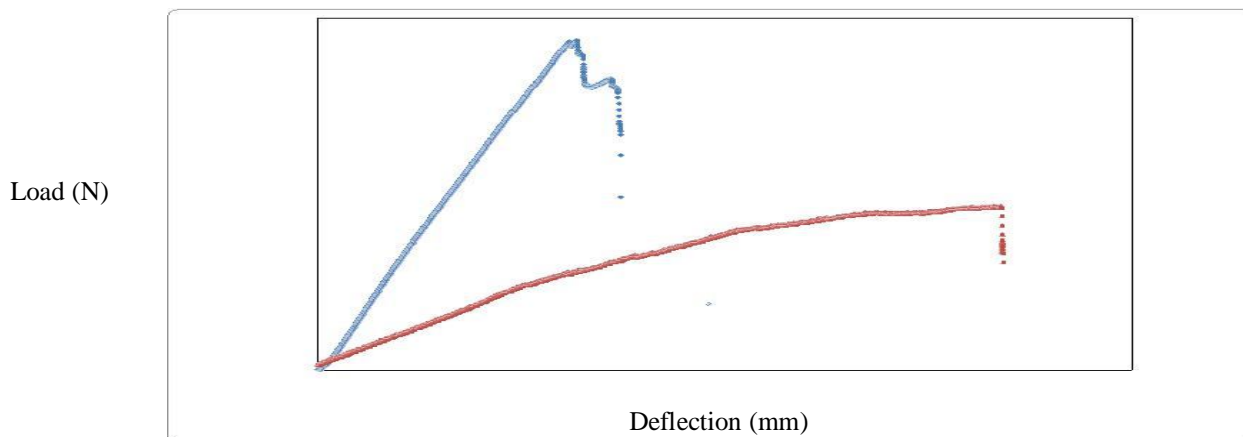


Figure 6: Load-deflection curve of the 3 laminates.

Mainly governed by: number of layers, fiber direction, grammage, strength and modulus of the fibers and the effectiveness of the bonding strength between matrix and fibers in transferring stress across the interface [27]. Figure 5 shows the stress-strain diagram for Hybrid jute/ Glass and Woven glass fabric reinforced composites. From the behavior observed, the strain is proportional to the load applied and increases linearly till reaching the maximum load where it exhibits a little non-linearity before its failure by progressive breaking of the fibers. During the tensile test, the Hybrid Jute/Glass fabric reinforced composites had a width-wise failure perpendicular to the force application axis. In the other hand, the transverse matrix cracking is the first failure mode seen. Hybrid Jute/Glass Fiber reinforced laminates showed catastrophic failure, compared to that of the totally synthesized one, with a violent release of elastic energy that caused explosion of the specimens in their centers. Tensile strength, tensile modulus and elongation at break of the three types of samples are presented in Table 3.

**B. Flexural strength test**

The flexural properties were obtained and are shown on load-displacement characteristic curves of the two laminates Figure 6. Samples with span ratio of 16 as suggested by ASTM D790, and five samples were tested for each laminate.

The modulus of rigidity and flexural strength of Hybrid Jute/Glass fabric reinforced laminate were better than those of the other reinforced with synthetic fabrics. Similar to tensile tests, the failure of Hybrid reinforced laminates took place abruptly while it happened gradually for the synthesized specimens. The final flexural fracture was caused by simultaneous compressive and tensile failure, on the upper and the inferior layers respectively. The flexural characteristics were lower than that of tension. One possible explanation of this fact is that the laminated composites were not fully loaded in flexion as it did under tensile loading [28].

The ratio between tensile strength and flexural fatigue of the Hybrid composites was 6,8 and 1,8 for synthesized ones and that explains the better flexural behavior of the Hybrid Jute/Glass composites than its tensile one. (Table 4).

**C. Short Beam Test**

ASTM D2344 specimens were cut with lengths resulting in a span/ thickness ration of 3 for the three types of composites laminates. The span was chosen in order to avoid flexural effects that could change the desired shear failure mode. Typical load-deflection curves for five samples subjected to shear strength tests are shown in Figure 7. As per the flexural fatigue test and tensile test are interlaminar shear strength and modulus of Glass fibers reinforced laminates was better than that of natural fibers. This is due to the poor interfacial adhesion because of hydrophilic nature of natural fiber in contrast of the hydrophobic character of polymer binder [28,29]. Accordingly, this fact causes the weakness of bonding between fibers and matrix, which is the main controller of the strength to shear. The average ILSS test results are as shown in Table 5. Another difference is that the laminates reinforced with synthesized fibers are better performance than those totally reinforced with natural fibers has been proved in our previous work. The averaged ILSS of the Hybrid fabric reinforced laminates was  $1226 \pm 100$  (N).

**IV. CONCLUSIONS**

The effect of reinforcement fabric nature on the mechanical behavior of two types of composite laminates was examined. Generally, the mechanical properties of obtained synthesized composites are higher than those of Natural fabric reinforced one. According to the experimental test results, the Jute/glass Hybrid fiber reinforcement is very strong to be introduced in composite laminates with thermosetting matrix. Although the Jute fibers have a rough surface, their bonding strength with polymer matrix is weak requiring prior chemical treatments. The Flexural fatigue characteristics and Interlaminar Shear properties of the Hybrid laminate were better than those of the synthetic reinforced one even though tensile properties of this latter were better than those of the Hybrid laminate. The Incorporation of natural fibers with GFRP can improve the properties and used as an alternate material for glass fiber reinforced polymer composites.

Reinforcement type	Flexural Load (N)	Flexural modulus (GPa)
Hybrid Jute/Glass Laminate	$532.8 \pm 47$	$2.4 \pm 0.26$
2D E-Glass Fabric	$275.6 \pm 20$	$10.02 \pm 1.2$

Table 4: Flexural characteristics of the laminates.

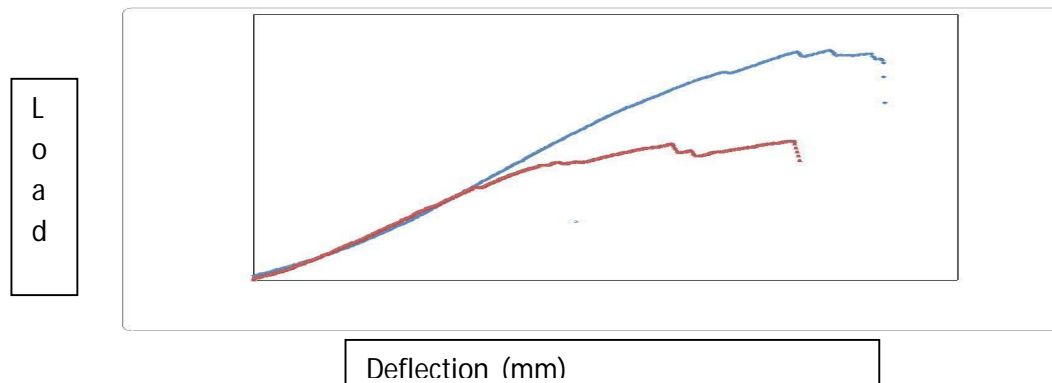


Figure 7: Load-deflection of ILSS test.

Reinforcement type	Interlaminar Shear Strength (MPa)
Jute Fabric	1223 ± 100
2D E-Glass Fabric	749 ± 61

Table 5: Inter-laminar shear strength properties of the samples.

The Hybrid Jute/Glass fiber reinforced polymer composites can be a agreed alternative to their synthesized homologue because they have beneficial properties such as low density, less expensive, thus, providing advantages for utilization in commercial applications automotive industry, buildings and constructions.

### REFERENCES

- [1] Jérémie A (2009) Comparative study of the behavior of composite thermosettingor thermoplastic matrix. Doctoral thesis, 1: 219.
- [2] Vijay KT, Manju KT (2014) Processing and characterization of natural cellulosefibers/thermoset polymer composites. Carbohydrate Polymer 109: 102-117.
- [3] Jian-He X, Ruo-Lin H (2012) Experimental study on rehabilitation of corrosion-damaged reinforced concrete beams with carbon fiber reinforced polymer. Construct and Build Mater 38: 708-716.
- [4] Ajith G, Senthil KM, Elayaperumal A (2014) Experimental Investigations onmechanical properties of jute fiber reinforced composites with polyester andepoxy resin matrices. ProcediaEng 97: 2052-2063.
- [5] Konstantinos G (2013) Inelastic behavior of polymer composites, DoctoralThesis, Lulea University of Technology, 9: 184.
- [6] Ramesh M, Palanikumar K, Hemachandra RK (2013) Mechanical propertyevaluation of sisal-jute-glass fiber reinforced polyester composites. Composites:Part B, 48: 1-9.
- [7] Christopher CL, Christian EO, Chris IO (2013) Natural fiber composite designand characterization for limit stress prediction in multiaxial stress state. Articlein press. J King Saud University-Engineering Sciences.
- [8] Emanuel MF, Vitor MC, Joao FM, Rui LR (2013) Novel cork-polymer compositesreinforced with short natural coconut fibers: Effect of fiber loading and couplingagent addition. Composites SciTechnol 78: 56-62.
- [9] Umar N, Jamil H, Megat AMHH (2015) A review on tribological performance ofnatural fibrepolymeric composites. Tribology Int 83: 77-104.
- [10] Lazaros T, Subhas D, Sandip R, Dieter F, Edith M et al. (2014) High Performancenatural rubber composites with a hierarchical reinforcement structure of carbon
- [11] Andrzej KB, Wenyang Z, Andris C (2001) Natural-fibre-reinforced polyurethane
- [12] Raghad HM, Mustafa AH, Noor SS (2010) The edition effect of natural fibres onpolymericmaterials and study some of thermal and mechanical properties. J
- [13] Amar SS, Vijay KTH (2008) Fabrication and study of lignocellulosic HibiscusSabdarriffaber reinforced polymer composites, peer-reviewes article. Bio
- [14] Pruttipong P, Warunee A, Tawatchai M, Rattiyakom S, Ketsara A, et al.(2014) Effect of modified jute fiber on mechanical properties of green rubbercomposite. Energy Procedia 56: 641-647.
- [15] Singh B, Gupta M, Anchal V (2000) The durability of jute fibre-reinforcedphenolic composites. Composites Sci and Technol 60: 581-589.
- [16] Giuseppe C, Alberta L, Giuseppe R, Gianluca C (2010) Composites based onnatural fibrefabrics, Woven fabric Engineering. PolonaDobnikDubrovski (ed).ISBN: 978-953-307-194-7, Intech.
- [17] Sukhdeep S, Dharpal D, Lakshya A, Gupta VK (2014) Tensile and flexuralbehavior of hemp fiber reinforced virgin-recycled HDPE matrix composites.Procedia Mater Sci 6: 1696-1702.
- [18] La SDE, Et T (2013) Analysis of the feasibility of eco-design of composite parts based on renewable resources for medical purposes.
- [19] Layth M. Ansari MNM, Grace P, Mohamed J, Islam MS (2015) A review onnatural fiber reinforced polymer composite and its applications, Hindawipublishing corporation. Int J Polymer Sci 15.
- [20] RezaurMd R, MonimulMd H, NazulMd MH (2008) Improvement of physic-mechanical properties of jute fiber reinforced polypropylene composites bypost-treatment. Composites: Part A, 39: 1739-1747.
- [21] Gianluca C, Giuseppe C, Giuseppe R, Alberta L (2010) Composites based on
- [22] Andrzej KB, Wenyang Z, Andris C (2001) Natural-fibre-reinforced polyurethanemicrofoams. Composites Scitechnol 61: 2405-2411.
- [23] Essabir H, Boujmal R, Ouadi M, Rodrigue D, Bouhfid R (2016) Mechanics ofmaterials mechanical and thermal properties of hybrid composites: Oil-palmfiber/clay reinforced high density polyethylene 98: 36-43.
- [24] Sanjay MR, Arpitha GR, Yogesha B (2015) Study on mechanical properties ofnatural - glass fibre reinforced polymer hybrid composites: A review. MaterialsToday: Proceedings 2: 2959-2967.
- [25] Gowda TM, Naidu ACB, Rajput C (1999) Some mechanical properties of untreated
- [26] Mustapha B, Abderrezak B, Katarzyna B, Fabrizio S, Stuart B (2013) Cactusfibre/polyester biocomposites: Manufacturing, quasi-static mechanical anfatigue characterization. Composites Scitechnol 74: 150-159.
- [27] Hind A, Hala B, Jamal E, Rachid B, Abouelkacem Q (2015) Fabrication,Charcaterization and modeling of laminated composites based on woven jute
- [28] Pruttipong P, Warunee A, Tawatchai M, Rattiyakom S, Ketsara A, et al. (2014) Effect of modified jute fiber on mechanical properties of green rubber composite. Energy Procedia 56: 641-647.
- [29] Moyeenuddin AS, Kim LP, Alan F (2012) Flexural properties of hemp fibre reinforced polylactide and unsaturated polyester composites. Composites: PartA 43: 519-526.





10.22214/IJRASET



45.98



IMPACT FACTOR:  
7.129



IMPACT FACTOR:  
7.429



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24\*7 Support on Whatsapp)