



IJRASET

International Journal For Research in
Applied Science and Engineering Technology



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Volume: 3 Issue: VI Month of publication: June 2015

DOI:

www.ijraset.com

Call:  08813907089

E-mail ID: ijraset@gmail.com

Optimization of Multi-pass Turning Parameters by Response Surface Methodology

Amey S. Kulkarni¹, Mukund V. Kavade²

¹M.Tech Student, Department of Mechanical Engineering, Rajarambapu Institute of technology, Rajaramnagar, Islampur, (India)

²Professor, Rajarambapu Institute of technology, Rajaramnagar, Islampur, (India)

Abstract- This paper elaborates the optimization of multi-pass turning process parameters by using design of experiment tool viz. response surface methodology. Three process parameters that are cutting speed, feed and depth of cut are taken into account for the optimization procedure intended to minimize the surface roughness and to maximize material removal rate. Multi-pass turning, where multiple passes are used for rough turning operation and single pass is used for finishing operation.

Keywords— Response Surface Methodology, Multi-pass Turning, Optimization

I. INTRODUCTION

The machining processes are commonly used in industries to produce components with high quality and also having cost effectiveness. Also these components not only have simple operations but also varying complex geometry. So to select appropriate combination of process parameters is important key to achieve quality as well as low cost. Single pass turning operations doesn't allow us to optimize the rough cut and finish cut independently so that multi-pass turning operations has advantage over single pass turning operation.

Suleyman Neseli et. al. [1] focuses on the influence of tool geometry on the surface finish obtained in turning of AISI 1040 steel. In order to find out the effect of tool geometry parameters on the surface roughness during turning, response surface methodology (RSM) was used and a prediction model was developed related to average surface roughness (Ra) using experimental data.

Makadia and Nanavati [2] used design of experiments to study the effect of the main turning parameters such as feed rate, tool nose radius, cutting speed and depth of cut on the surface roughness of AISI 410 steel.

Naga Phani Sastry et al. [3] set the three levels of the feed, three levels of speed, three values of the depth of cut, two different types of work materials and have been used to generate a total 20 readings in a single set. After having the data from the experiments, the performance measures surface roughness (Ra) of the test samples was taken on a profilometer and MRR is calculated using the existing formulae.

Gowd et. al. [4] applied the Response Surface Methodology (RSM) to accurately predict the mathematical models to estimate feed force, thrust force, cutting force and surface roughness on Inconel 600.

II. RESPONSE SURFACE METHODOLOGY (RSM)

Response surface methodology^[1] is the strategy of doing experiments in order to optimize the target response, for which it uses the statistical and mathematical techniques. The relation between input and output response is postulated in low degree polynomial as

$$y = f(x_1, x_2) + \varepsilon$$

Where ε is error or noise?

Here, we used the central composite design (CCD) which comprises 2^3 factorial designs wherein α value kept as 1.633 to get rotatability feature of CCD. The value of α is selected such that CCD should not be in face centred because these designs are not rotatable.

III. METHODOLOGY

In this paper, response surface methodology is used to optimize the response; surface roughness and material removal rate. Turning process is mainly influenced by three main process parameters and they are namely cutting speed, feed and depth of

International Journal for Research in Applied Science & Engineering Technology (IJRASET)

cut. And parameters upper and lower bounds are selected accordingly and are easily understandable by table given below,

Table No.1: Cutting Data

	Cutting Speed (rpm)	Feed (mm/rev)	Depth of Cut (mm)
Upper Bound	875	0.1	0.2
Lower Bound	2000	1.0	1.0

Specimen material chosen was EN8 (080M40) because of wide application for industrial purpose. It is in round bar shape of having 40mm diameter. But 39mm was taken and 1mm relaxed for oxidation layer, stains etc. Machining was done by TNMG Cutting tool with nose radius 0.8mm. Machining was carried out on CNC Turning Centre consequently the experiments as specified in table no.2.

IV. OBJECTIVE FUNCTION

Here, area of interest is mainly on minimizing the Ra (μm) value of surface roughness and maximizing the material removal rate (MRR) ($mm^3/min.$) in order to get high quality surface finish with higher MRR.

A. Surface roughness

This response is largely influenced by feed rate and tool nose radius and related by

$$R_{max} = \frac{0.0321f^2}{r}$$

Where, R_{max} = maximum height of profile

r = Tool nose radius

Beside of above two parameters, cutting speed and depth of cut also take part in influencing the surface roughness value. Here, we kept the tool nose radius as constant parameter value.

B. Material removal rate

The aim of any turning experiment is maximizing MRR And to achieve that it is necessary to obtain optimal combination of cutting speed, feed and depth of cut. MRR is function of above said parameters and related as

$$MRR = v \times f \times d \quad \text{in } mm^3/min,$$

Where, v = cutting speed

f = feed and

d = depth of cut

V. RESULTS AND DISCUSSION

Second order model is used for analysis in respect to effect of input variables on output variables because second order model uses a quadratic term which helps to get curvature of output response. Results generated by Minitab 16 software are discussed and interpreted in this paper. Contour plots and surface plots are drawn by using mentioned software are presented and interpreted in successive pages. Contour plot of surface roughness is indicated by figure 1 shows the various optimal combinations of three parameters over surface roughness value

International Journal for Research in Applied Science & Engineering Technology (IJRASET)

Table No. 2: Run order of experiment and their responses

Standard Order	Run Order	Cutting Speed	Feed	Depth of Cut	Surface Roughness (μm)	Material Removal Rate ($\text{mm}^3/\text{min.}$)
12	1	1469	0.5500	0.600	3.166	484.77
2	2	1819	0.2744	0.330	3.237	164.714
6	3	1819	0.2744	0.854	2.512	426.260
7	4	1119	0.8256	0.854	3.198	788.965
11	5	1469	0.5500	0.600	5.841	484.770
1	6	1119	0.2744	0.330	3.969	101.328
8	7	1819	0.8256	0.854	4.388	1282.509
4	8	1819	0.8256	0.330	6.131	495.583
10	9	1469	0.5500	0.600	8.746	484.770
9	10	1469	0.5500	0.600	3.025	484.770
3	11	1119	0.8256	0.330	13.619	304.869
5	12	1119	0.2744	0.854	2.310	262.224
14	13	2040	0.5500	0.600	3.328	673.200
15	14	1469	0.1000	0.600	3.837	88.140
13	15	898	0.5500	0.600	6.709	296.340
19	16	1469	0.5500	0.600	7.965	484.77
16	17	1469	1.0000	0.600	14.613	881.40
17	18	1469	0.5500	0.200	8.702	161.59
18	19	1469	0.5500	1.000	9.654	807.95
20	20	1469	0.5500	0.600	9.424	484.77

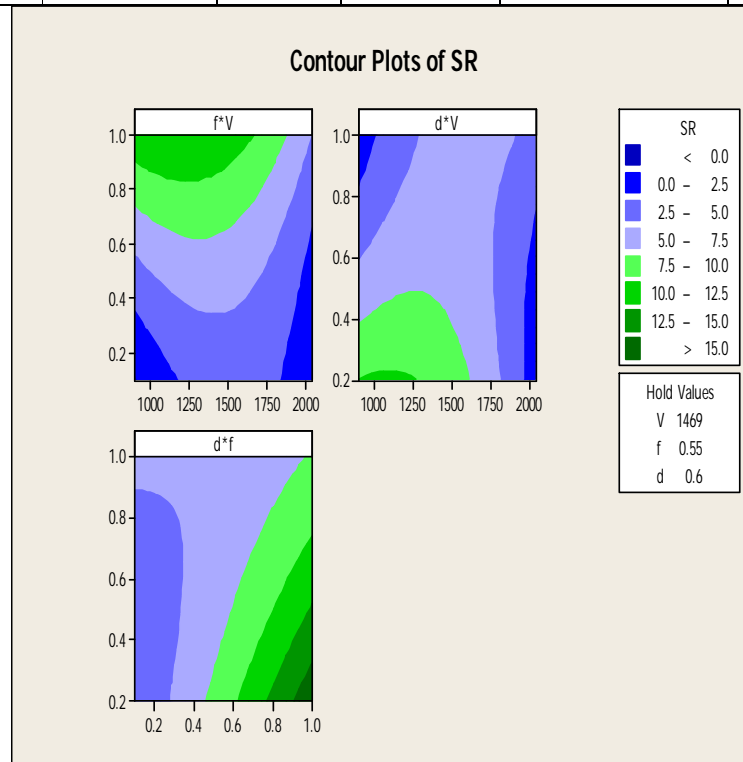


Figure 1: Contour plots of Surface Roughness

International Journal for Research in Applied Science & Engineering Technology (IJRASET)

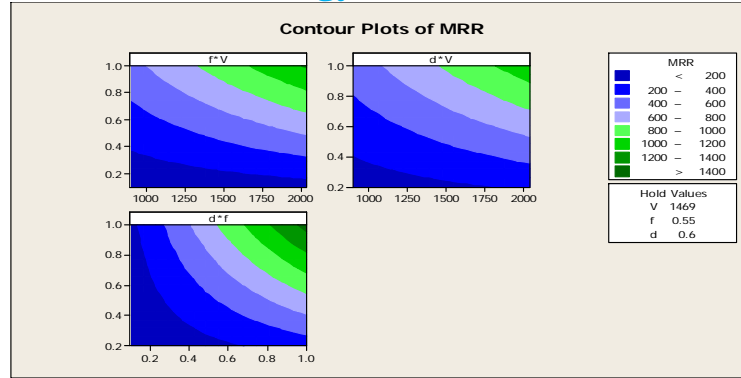


Figure 2 : Contour plots of Material Removal Rate (MRR)

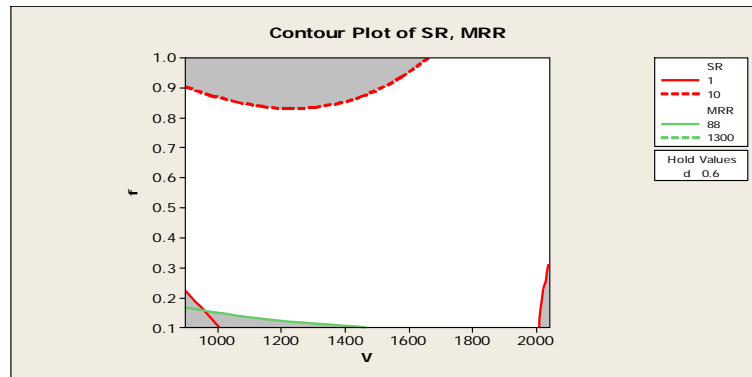


Figure 3: Overlaid contour plots of Surface Roughness and Material Removal Rate

Blue coloured region on feed vs. Cutting speed plot and on depth of cut vs. Cutting speed plot gives the optimal combination of variables which denotes that feed in range of 0.1 to 0.35 mm/rev. At cutting speed in range of 875 to 1200 rpm attains optimal solution. On another graph of depth of cut vs. cutting speed gave out optimal solution ranging where depths of cut get from 0.82 to 1mm and where cutting speed 1950 to 2000rpm. Surface plot clears it by plotting 3 dimensional graph showing dipping surface gives lower surface roughness.(Not included in this paper). So by setting values between this regions gave the output in terms of best surface finish. A contour plot in of MRR (figure no.2) denotes that by keeping all parameter values at higher levels we can surely get higher MRR. Green shades are self explanatory about setting the combination suitable to get higher MRR in case of rough cuts. Overlaid contour plot (refer figure no. 3) of surface roughness and material removal rate is drawn so that it will give idea about to maintain parameter values in white region in order to get best response.

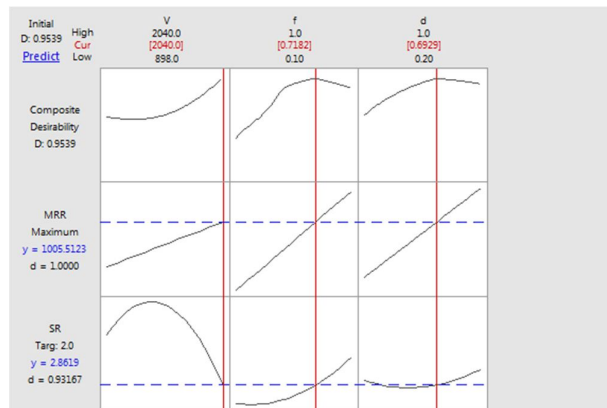


Figure 4: Plot by response optimizer

International Journal for Research in Applied Science & Engineering Technology (IJRASET)

Response optimizer tool in Minitab software generated the plot to get variables at optimal combination and the same self explained in figure 4.

VI. CONCLUSION

All discussed points above are concluded in the manner that the three parameters; cutting speed, feed and depth of cut values must be different for rough cut operation and finish cut operation. But here we defined the variable levels for improving MRR and surface roughness was kept at targeted value of $2.00\mu\text{m}$. Hence according to desired response to obtain best results we may set the target for any response to optimize another response variable and same is achieved by using response optimizer. Table number

Table No. 3: Optimized input variables

Variable	Setting
v	2040
f	0.718182
d	0.692929

REFERENCES

- [1] Suleyman Neseli, Suleyman Yaldız, Erol Turkes (2011) Optimization of tool geometry parameters for turning operations based on the response surface methodology, *Measurement* 44, 580–587
- [2] Ashvin J. Makadia, J.I. Nanavati (2013) Optimisation of machining parameters for turning operations based on response surface methodology, *Measurement* 46, 1521–1529.
- [3] Dr. M. Naga Phani Sastry, K. Devaki Devi, Dr. K. Madhava Reddy (2012) Analysis and Optimization of Machining Process Parameters Using Design of Experiments, *Industrial Engineering Letters*, 2(9), 23-32.
- [4] Dr. G.Harinath Gowd, M. Gunasekhar Reddy, Bathina Sreenivasulu (2012) Empirical modeling of Hard Turning process of Inconel using Response Surface Methodology, *International Journal of Emerging Technology and Advanced Engineering*, 2(10), 498-504.
- [5] Montgomery Douglas C. (2010) *Design and Analysis of Experiment*, 5th edition, Wiley, 417-485.



10.22214/IJRASET



45.98



IMPACT FACTOR:
7.129



IMPACT FACTOR:
7.429



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24*7 Support on Whatsapp)