



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Volume: 8 Issue: XI Month of publication: November 2020

DOI: https://doi.org/10.22214/ijraset.2020.32031

www.ijraset.com

Call: © 08813907089 E-mail ID: ijraset@gmail.com



ISSN: 2321-9653; IC Value: 45.98; SJ Impact Factor: 7.429

Volume 8 Issue XI Nov 2020- Available at www.ijraset.com

Parametric Study of the TIG Welding Parameter for SS317L Steel

Sushant Pardeshi¹, Mukesh Dubey²

¹MTech Scholar, BIT DURG, C.G., INDIA,

²Associate Professor, BIT DURG, C.G., INDIA

Abstract: In this research work the experimental investigation of TIG welding process on ss317 alloy pipe with different process parameter viz. Welding current, voltage, and gas flow rate with L-9 orthogonal array design of experiment. Bending and Tensile test are performed for all 9-test sample as an output parameter. Optimization of process parameter is done via ANOVA and Taguchi method using MINITAB 18 software.

The optimum values of input parameter for tensile strength during TIG welding are 65A current,25V voltage, and 16 lit/s Gas flow rate and for Bending strength the optimum input process parameter are 60A current, 25V voltage, and 16 lit/s Gas flow rate. It has been observed that welding current affects the tensile strength maximum 77.92% followed by voltage 11.18 %. GFR has minimum affect only 7.10% and It can be also observed that voltage affect the Bending strength maximum 37.129% followed by GFR 32.21%. Welding current has minimum affect only 18.06%. The paper ends with a comparison of optimum process parameter of Taguchi and ANOVA method.

Keywords: TIG welding, SS317, optimization, Tensile strength, Taguchi and ANOVA method.

I. INTRODUCTION

Aluminum composite has good mechanical characteristic (better strength, light weight, etc.) hence they are used in aerospace, automobile industries, defense etc. [1]. Welding is the method of joining of two similar or dissimilar metal or alloy joins together with the application of heat, pressure or both [2].

Tungsten inert gas welding (TIG) was developed by Russel Meredith which was used for the welding of magnesium in year 1941 [3]. In TIG welding process electrode is made of Tungsten which is non consumable one weld is protected by flow of inert gases [4]. A filler rod may be fed to arc zone [5].

A shielding of inert gas most commonly used argon and helium. Inert gas is utilized for the avoid the atmospheric contamination of the weld pool [5]. Heat input parameter play significant role on the cooling rate; bead size and mechanical properties of the weld [6]. TIG weld quality is unequivocally portrayed by the weld pool geometry on the because the weld pool geometry plays a significant role to deciding the mechanical properties of weld [7-8].

Singh et.al 2017 [1] utilized Activated Flux TIG (ATIG) welding process for joining of P91 Steel (Ferritic Steel) plates. Initiating transition (a meager layer) is applied along the line on the outside of the material where the welding is to be completes in this procedure. Jadon et.al 2017 [2] carried out bead on plate welds for Mild Steel and AISI 409 platesutilizing Gas tungsten arc welding (GTAW) technique.

Sharma et.al 2017 [3] In this paper optimization of TIG welding process parameters on Stainless Steel 347, 321 Stainless Steel by using various optimization methods like analysis of variance (ANOVA). Kanaiya et.al 2017 [4] this paper gives an overall view of the TIG welding process and its equipment. Hussein et.al 2016 [5] This exploration researches the procedure properties relationship of welded tube of mild steel (MS) with unique thickness by utilizing TIG welding.

II. EXPERIMENTAL STUDY

The raw material for this experiment is SS317L pipe. Table 1 describes the dimension of the selected plates. For this research work TIG welding machine TORNADO TIG 315 (figure 1) setup available at Rungtacollege of Engineering and Technology, Bhilai workshop. After the cutting the plates into 18 numbers of pieces the edge of plates is grinded. The input process parameters Welding current, voltage, and gas flow rate is set to the selected machine according to design of experiment table. The measured bending and tensile strength of sets of 9 welded plates is sown in table 2.

ISSN: 2321-9653; IC Value: 45.98; SJ Impact Factor: 7.429 Volume 8 Issue XI Nov 2020- Available at www.ijraset.com

Table 1. Dimension of selected pipe

| Outer diameter(mm) | 13 |
|---------------------|-------|
| Inner diameter (mm) | 12.5 |
| Thickness(mm) | 0.5 |
| Length of pipe (mm) | 203.2 |
| Number of pipes | 18 |

Table 2. Chemical composition of SS317

| Material | С | Mn | Si | Cr | Ni | Mo | P | S | N | Fe |
|-----------|-------|------|------|--------|--------|-------|-------|-------|------|--------|
| SS316L | | | | | | | | | | |
| Stainless | 0.030 | 2.00 | 0.75 | 16.00- | 10.00- | 2.00- | 0.045 | 0.030 | 0.10 | 69.045 |
| steel | | | | 18.00 | 14.00 | 3.00 | | | | |



Fig. 1.Complete TIG welding set up

III. ANOVA

ANOVA is a statistically based, objective decision-making tool for detecting any differences in the average performance of groups of items tested. ANOVA helps in formally testing the significance of all main factors and their interactions by comparing the mean square against an estimate of the experimental errors at specific confidence levels.

IV. OPTIMIZATION OF TIG WELDING PROCESS PARAMETERS

TIG welding experimental values are optimized using Taguchi orthogonal array and ANOVA and the effects of individual TIG welding process parameters on the selected quality characteristics are calculated separately

A. Effect on Tensile strength

To describe the effect of various input parameters (current, welding speed, GFR) on tensile strength the experiment is conducted using L-9 orthogonal array. S/N ratio of optimized tensile strength value is shown in table 3.



ISSN: 2321-9653; IC Value: 45.98; SJ Impact Factor: 7.429 Volume 8 Issue XI Nov 2020- Available at www.ijraset.com

Table 3.Experimental data related to TIG Welding.

| Exp | | Input paramete | r | Output parameter | | | |
|-----|-------------|----------------|---------------|------------------|----------|-----------|--------------|
| No | Starting | Welding | Gas flow | Tensile | Bending | S/N ratio | S/N ratio BS |
| | Welding | speed | rate(lit/sec) | Strength | Strength | TS | |
| | current (A) | (mm/s) | | MPa | MPa | | |
| | | | | | | | |
| 1 | 55 | 20 | 16 | 746.502 | 101.68 | 57.4606 | 40.1447 |
| 2 | 55 | 25 | 18 | 787.478 | 109.66 | 57.9247 | 40.8009 |
| 3 | 55 | 30 | 20 | 735.223 | 68.33 | 57.3283 | 36.6922 |
| 4 | 60 | 20 | 18 | 735.812 | 76.66 | 58.5452 | 37.6913 |
| 5 | 60 | 25 | 20 | 806.245 | 106.33 | 58.1293 | 40.5331 |
| 6 | 60 | 30 | 16 | 791.875 | 109.89 | 57.9731 | 40.8191 |
| 7 | 65 | 20 | 20 | 844.2 | 70.33 | 58.5289 | 36.9428 |
| 8 | 65 | 25 | 16 | 873.89 | 99.33 | 58.8291 | 39.9416 |
| 9 | 65 | 30 | 18 | 834.33 | 70.68 | 58.4324 | 36.9859 |

Table 4.ANOVA table of Tensile strength (S/N data)

| Tuble in the virtuable of Tensile Strength (S/T) data) | | | | | | |
|--|----|---------|---------|---------|---------|--|
| Source | DF | Adj SS | Adj MS | F-Value | P-Value | |
| Current | 2 | 1.61256 | 0.80628 | 20.66 | 0.046 | |
| Voltage | 2 | 0.23152 | 0.11576 | 2.97 | 0.252 | |
| GFR | 2 | 0.14711 | 0.07356 | 1.88 | 0.347 | |
| Error | 2 | 0.07805 | 0.03903 | | | |
| Total | 8 | 2.06925 | | | | |

It can be observed from the table 4 that welding current affect the Tensile strength maximum 77.92% followed by voltage 11.18 %. GFR has minimum affect only 7.10% and graph is shown in figure 3.

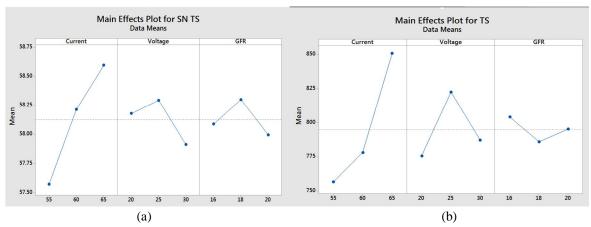


Figure 3. (a)Effect of process parameters on Tensile strength (S/N data) (b) Effect of process parameters on tensile strength (Raw data)



International Journal for Research in Applied Science & Engineering Technology (IJRASET)

ISSN: 2321-9653; IC Value: 45.98; SJ Impact Factor: 7.429

Volume 8 Issue XI Nov 2020- Available at www.ijraset.com

Effect on Bending Strength

To describe the effect of various input parameters (current, welding speed, standoff distance) on tensile strength the experiments are conducted using L-9 orthogonal array. S/N ratio of optimized tensile strength value are shown in table 5.

Table 5. ANOVA table for bending strength (S/N data)

| Source | DF | Adj SS | Adj MS | F-Value | P-Value |
|---------|----|--------|--------|---------|---------|
| Current | 2 | 4.770 | 2.385 | 1.44 | 0.411 |
| Voltage | 2 | 9.804 | 4.902 | 2.95 | 0.253 |
| GFR | 2 | 8.507 | 4.253 | 2.56 | 0.281 |
| Error | 2 | 3.324 | 1.662 | | |
| Total | 8 | 26.405 | | | |

It can be observed from the table 5 that voltage affect the Bending strength maximum 37.129% followed by GFR 32.21%. Welding current has minimum affect only 18.06% and graph is shown in Figure 4.

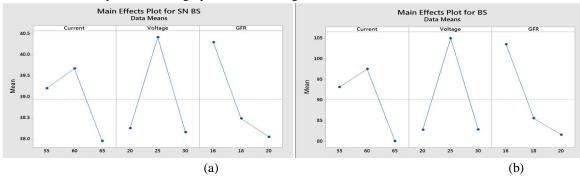


Figure 4. (a)Effect of process parameters on bending strength (S/N data) (b) Effect of process parameters on bending strength

V. CONCLUSION

This chapter provides the concluding remarks of the research work. In this research work the TIG welding process for steel 317 was carried out and through the study some important parameters were identified. These parameters are carefully altered through the design of experiment method. After that the optimization technique of ANOVA was implanted in order to get the better result for the output parameters. The change in parameters results in better welding tensile strength and bending strength.

REFERENCES

- Akhilesh Kumar Singh, Mayank Kumar, Vidyut Dey, Ram Naresh Rai [2017] "A study to increase weld penetration in p91 steel during TIG welding by using activating fluxes" IOP Conf. Series: Materials Science and Engineering 225(2017) 012099.
- Anurag singhjadon, Nishant singhkushwah, Pavan agrawal, Promise mittal [2017] "Parametric Optimization of GTAW Welding Using Taguchi and ANOVA" International Journal for Research in Applied Science & Engineering Technology (IJRASET) Volume 5 Issue IX, September 2017 www.ijraset.com.
- Kamalkantsharma, Indraj Singh [2017] "Optimization of gas tungsten arc welding on steel A review" International Journal of Interdisciplinary Research Volume 3, Issue 1, March 2017.
- [4] Devang R.Kanaiya, Pankaj Rathod [2017]"Design and Simulation of Orbital Welding Head used in Welding Pressure Vessel Tube -A Review" International Journal of Engineering Technology Science and Research Volume 4, Issue 4 April 2017 www.ijetsr.com
- N. I. S. Hussein, M. N. Ayof, and S. Nordin [2016] "Tensile Strength of Welded Mild Steel Tubes with Dissimilar Thickness" International Journal of Materials, Mechanics and Manufacturing, Vol. 4, No. 1, February 2016.
- M.Karthikeyanl, Vallayil N. A Naikan, R. Narayan and D.P.Sudhankar [2016] "TIG Welding Process Parameter Optimization using Design of Experiment for Satellite Application" International Journal of Performability Engineering, Vol. 12, No. 2, March 2016. pp. 155-172. © Totem Publisher, Inc., 4625 Stargazer Dr., Plano, Texas 75024, U.S.A.
- Gurdev singh1, Aman Bansal, Dr Amit kumar Gupta, Amandeep singh [2016] "Study the parametric optimization of TIG welding" Research Journal of Engineering and Technology (IRJET) e-ISSN: 2395 -0056 Volume: 03 Issue: 05 | May-2016 www.irjet.net.
- Omkar Joshi, Dr. Arun kumar [2015] "Overview of Orbital Welding Technology" International Journal of Innovative Science, Engineering & Technology, Vol. 2 Issue 12, December 2015 www.ijiset.com
- ErBhawandeepsingh, Er Avtar simgh [2015] "Performance of activated TIG process in mild steel welds" Journal of Mechanical and Civil Engineering (IOSR-JMCE) Volume 12, Issue 2 Ver. IV (Mar - Apr. 2015), PP 01-05 www.iosrjournals.org.
- Amit Kumar, Mohd Majid [2015] "To Study The Effect Of SiO2 In A-GTAW Welded Joint Made On Stainless Steel AISI SS 304" International Journal For Technological Research In Engineering (IJTRE) Volume 2, Issue 7, March-2015.









45.98



IMPACT FACTOR: 7.129



IMPACT FACTOR: 7.429



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call: 08813907089 🕓 (24*7 Support on Whatsapp)