



# **iJRASET**

International Journal For Research in  
Applied Science and Engineering Technology



---

# **INTERNATIONAL JOURNAL FOR RESEARCH**

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

---

**Volume: 5      Issue: VIII      Month of publication: August 2017**

**DOI: <http://doi.org/10.22214/ijraset.2017.8290>**

**[www.ijraset.com](http://www.ijraset.com)**

**Call:  08813907089**

**E-mail ID: [ijraset@gmail.com](mailto:ijraset@gmail.com)**

# Swift Heavy Ion Induced Opto-Effects in Ethylene-Chlorotrifluoroethylene Copolymer (E-CTFE)

Kusam Devgan

Department of Physics, S.R. Government College For Women

Amritsar, Punjab, India.

**Abstract**---The results due to ion induced effects in the optical properties of pristine and lithium ion irradiated ethylene-chlorotrifluoroethylene (E-CTFE) samples have been studied. Samples were irradiated in vacuum at room temperature by lithium (50 MeV) with the fluence in the range of  $1 \times 10^{11}$ – $3 \times 10^{12}$  ions  $\text{cm}^{-2}$ .

**Keywords:** Polymer; irradiation; thin films; crosslinking; UV-Visible.

## I. INTRODUCTION

E-CTFE (ethylene-chlorotrifluoroethylene) copolymer is produced by combining  $\text{CH}_2\text{-CH}_2$  and  $\text{CClF-CF}_2$  co-monomer entity alternatively. Ion irradiation of polymers can induce irreversible alterations in their macroscopic properties such as electrical and optical properties [1]. Interest in ion beam treatment of polymers has increased in recent years, prompted by the ion beam induced improvements of the mechanical, optical and electrical properties of various polymer substrates [2-4]. Chemical bond characterization and new induced properties in several polymers irradiated with different ions have been analyzed by Davenas et al. [5]. Modifications of polymers by irradiation, with ionizing radiation in particular, are an expanding field of research and application because of its technological implications. The modifications in the chemical structure and physico-chemical properties of polymers, induced by ion bombardment, are being extensively studied [6,7]. Different studies reveal that carbonaceous clusters are formed along latent tracks of energetic ions in polymers [8-10]. The formation of these carbonaceous clusters can be studied from the absorption edge of ultraviolet-visible (UV-Vis) spectra of irradiated polymers. UV-Vis spectroscopy gives an idea about the value of optical band gap ( $E_g$ ) with Tauc's expression [11].

## II. EXPERIMENTAL SECTION

The specimens of E-CTFE, in the form of flat polished films were procured from Good Fellow Ltd. (UK) having thickness range  $25\mu\text{m}$ . The films of E-CTFE were used as-received form without any further treatment in the size of  $1 \text{ cm} \times 1 \text{ cm}$ . The samples were mounted on the sliding ladder and irradiated with lithium (50 MeV) ion beams using 15 UD pelletron facility for the general purpose scattering chamber (GPSC) under vacuum of  $\sim 10^{-6}$  Torr at Inter-University Accelerator Center, New Delhi, India. The ion range, electronic energy loss and nuclear energy loss of characterize lithium (50MeV) ions in E-CTFE polymer is shown in table 1 [12]. The ion beam fluence was varied from  $1 \times 10^{11}$  to  $3 \times 10^{12}$  ions  $\text{cm}^{-2}$ . In order to expose the whole target area, the beam was scanned in the x-y plane. The beam current was kept low to suppress thermal decomposition and was monitored intermittently with a Faraday cup. The samples were analyzed with UV-VIS spectroscopy using Lambda 35 Perkin Elmer UV-Vis spectrophotometer in the range 200-800 nm to observe the variation in optical properties of the polymer. Doses for the given fluence and different studied ion types were calculated using the formula [13] as given below.

$$\text{Dose} = 1.602 \times 10^{-10} \times \frac{1}{\rho} \times \frac{dE}{dx} \times \phi \quad (1)$$

$\phi$  : Ion fluence,

$\rho$ : Density of polymer,

$\frac{dE}{dx}$  : Stopping power of ion

TABLE 1

ELECTRONIC, NUCLEAR ENERGY LOSS AND ION RANGE OF POLYMER				
Polymer	Ion Beam	Ion range (μm)	Electronic Energy loss (eV/Å)	Nuclear Energy loss (eV/Å)
ECTFE	Lithium (50MeV)	514.51	7.75	2.993 E-03

TABLE 2

DOSES FOR GIVEN FLUENCE AND ION TYPE OF STUDIED POLYMER		
Polymer	Ion Fluence (ions/cm <sup>2</sup> )	lithium (50 MeV) (kGy)
E-CTFE	Pristine	0.00
	1 x 10 <sup>11</sup>	7.38
	3 x 10 <sup>11</sup>	22.14
	1x10 <sup>12</sup>	73.81
	3 x 10 <sup>12</sup>	221.43

### III. RESULTS AND DISCUSSION

Fig. 1. depicts UV-Visible spectra of swift heavy ion irradiated E-CTFE films. It has been observed that there is shift in absorption edge from ultraviolet to visible region due to ion irradiation.

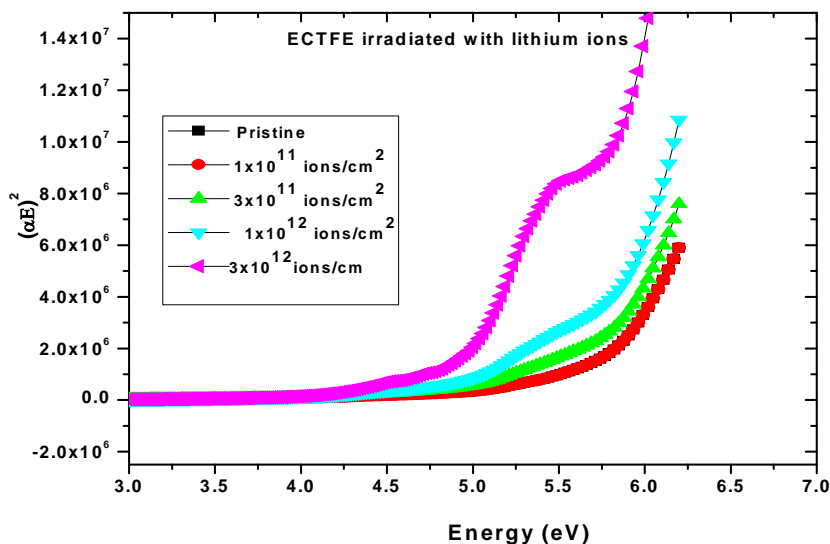


Fig 1. UV-VIS spectra of swift heavy ion irradiated E-CTFE at varying fluence.

It is also clear that there is decreasing trend of the optical band gap energy with increasing ion fluence in case of studied ion beam.

#### IV. CONCLUSION

Results summarized in this paper suggest that swift heavy ion irradiation of E-CTFE leads to its optical degradation.

#### V. ACKNOWLEDGMENT

IUAC (Inter-University Accelerator Center), New Delhi and Physics Department, Guru Nanak Dev University, Amritsar are acknowledged by the author for providing the swift heavy ion facility and UV Visible spectrometer.

#### REFERENCES

- [1] T. Hioki, S. Noda, M. Sugiura, M. Kakeno, K. Yamada, and J. Kawamoto, "Electrical and Optical Properties of Ion Irradiated Organic Polymer Kapton H," *Appl. Phys. Lett.* vol. 43, pp. 30-33, 1983.
- [2] E.H. Lee, In: M.K. Ghosh, and K.L. Mittal, (Eds.), *Polyimids: Fundamentals and Applications, Ion Beam Modification of Polyimides.* Marcel Dekker, New York, pp. 471-503, 1996.
- [3] T. Venkatesan, L. Calcagno B.S. Elman, and G. Foti, In: Mazzoldi, P., Arnoled, G.W. (Eds.), "Ion Beam Modification of Insulators," Elsevier, Amsterdam, pp. 301-310, 1987
- [4] L.S. Wielunski, R.A. Clissold, E. Yap, D.G. McCulloch, D.R. McKenzie, and M.V. Swain, "Mechanical and structural modification of CR-39 polymer surface by 50 keV hydrogen and argon ion implantation," *Nucl. Instrum. Methods B*, vol. 127/128, pp. 698-701, May, 1997.
- [5] J. Davenas, X.L. Xu, G. Boiteux, and D. Sage, "Relation between structure and electronic properties of ion irradiated polymers," *Nucl. Instrum. and Meth. B* vol. 39, pp.754-763, March. 1989
- [6] T.A. Tombrello, "Predicting latent track dimensions," *Nucl. Instrum. and Meth. B* vol. 94, pp. 424-428, Dec. 1994.
- [7] T. Steckenreiter, E. Balanzat, H. Fuess, and C. Trautmann, "Chemical modifications of PET induced by swift heavy ions," *Nucl. Instrum. and Meth. B* vol. 131, pp. 159-166, Aug. 1997.
- [8] D. Fink, W.H. Chung, R. Klett, A. Schmoldt, J. Cardosa, R. Montiel, M.H. Vazquez, L. Wang, F. Hosoi, H. Omichi, and P. Goppelt-Langer, "Carbonaceous clusters in irradiated polymers as revealed by UV-visible spectrometry," *Radiat. Eff. Def. Solids* vol. 133, pp. 193-208, Aug. 2006.
- [9] D. Fink, R. Klett, L.T. Chadderton, J. Cardosa, R. Montiel, H. Vezquez, and A. Karanovich, "Carbonaceous clusters in irradiated polymers as revealed by small angle X-ray scattering and ESR," *Nucl. Instrum. Methods Phys. Res. B* vol. 111, pp. 303-314, May. 1996.
- [10] J. Davenas, P. Thevenard, G. Boiteux, M. Fallavier, and X.L. Lu, "Hydrogenated carbon layers produced by ion beam irradiation of PMMA and polystyrene 4lms," *Nucl. Instrum. Methods Phys. Res. B* vol. 46, pp. 317-323, Feb. 1990.
- [11] S. Gupta, D. Choudhary, and A. Sarma, "Study of Carbonaceous clusters in irradiated polycarbonate with UV-Vis spectroscopy," *J. Polym. Sci. Part B. Polym. Phys.* vol. 38, pp. 1589-1594, May. 2000.
- [12] J.F. Ziegler and J.P. Biersack SRIM-IBM Research, New York. 2008.
- [13] O.B. Geiß, M. Kramer and G. Kraft, "Efficiency of thermo-luminescent detectors to heavy charged particles," *Nucl Instrum and Methds in Phys Res B*, vol. 142, pp. 592-598, Aug. 1998.



10.22214/IJRASET



45.98



IMPACT FACTOR:  
7.129



IMPACT FACTOR:  
7.429



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24\*7 Support on Whatsapp)