



# IJRASET

International Journal For Research in  
Applied Science and Engineering Technology



---

# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

---

**Volume: 5      Issue: IX      Month of publication: September 2017**

**DOI: <http://doi.org/10.22214/ijraset.2017.9096>**

**[www.ijraset.com](http://www.ijraset.com)**

**Call:  08813907089**

**E-mail ID: [ijraset@gmail.com](mailto:ijraset@gmail.com)**

# Optimization of CO<sub>2</sub> Laser Beam Cutting Process Parameters for Machining Of AISI 9255 Spring Steel

Renangi Sandeep<sup>1</sup>, S Bala Anki Reddy<sup>2</sup>, S Jaya Kishore<sup>3</sup>

<sup>1,2</sup>Assistant Professor, Department of Mechanical Engineering, Siddartha Institute of Science and Technology, Puttur, A.P., India – 517583

<sup>3</sup> Assistant Professor, Department of Mechanical Engineering, SVCE, Tirupathi, A.P., India – 517501

**Abstract:** The present work deals with the process parameters optimization of continuous wave CO<sub>2</sub> laser cutting of AISI 9255 spring steel. In the present study four process variables such as laser power, cutting speed, laser pressure and focal distance are considered and experimentation are carried out based on L<sub>27</sub> orthogonal array (OA). The cut quality responses such as surface roughness and kerf taper are measured for every experimental run. To optimize process parameters TOPSIS method is employed. The aim of optimization is to minimize surface roughness and kerf taper characteristics.

**Keywords:** CO<sub>2</sub> Laser beam cutting, spring steel, Kerf taper, TOPSIS, L<sub>27</sub> OA

## I. INTRODUCTION

The laser was developed in 1960s due to its precision and high intensity has been widely used in the field of fine cutting of sheet metals. Lasers remain well known and a very flexible mechanism for producing various micro-structures in this modern era, particularly in upgrading of engineering materials. Laser Beam Machining (LBM) is one of the innovative non-conventional machining process that actuality contemporarily used for shaping virtually entire range of engineering materials wherever complex shapes in request precise, fast and force-free processing. In addition, marking, drilling, and welding applications, cutting is the most irregularly useful LBM process.

Laser beam cutting is a non-contact type; thermal energy based unconventional machining process in which an excessive intensity laser beam is concentrated at a spot and material gets melted or evaporated at that spot. The molten metal was removed from the melting pool by supplying the high pressure co-axial assisted gas as show in Fig. 1. The efficiency of the laser cutting process be influenced by mechanical properties of the material to be cut and then also based on the thermal and some extent optical properties.

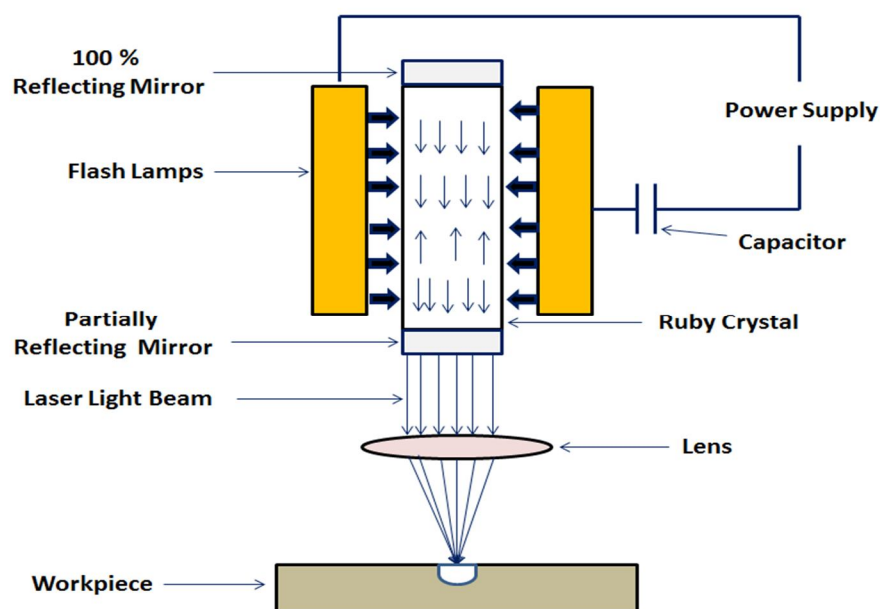


Fig. 1 Principle of Laser Beam Cutting Process

There are many researchers have been studied laser beam cutting process. Some of literatures are B S Yilbas [1] has studied the Striation formation due to the slow drifts and disturbances in various parameters during the laser cutting process. The effects of laser power, cutting speed and energy coupling factor on the kerf size are investigated. His work has shown that increasing laser power and energy coupling factor increase the kerf width size. Also, small changes in laser power, cutting speed and energy coupling factor modify the kerf width to a great extent. Dayana Espinal and Aravinda Kar [2] have developed A simple mathematical model to relate kerf depth to laser power, laser scanning speed and kerf width during laser cutting. Asano et al. [3] have shown that the range of processing conditions which allow cutting is determined by the energy input per unit area. The values of roughness of the cutting surface on both entry and exit sides of the plates can be reduced if the cutting speed is 1000 mm/min or higher. They change little at small values if the heat input per unit area is within a range under 20 J/mm<sup>2</sup>. Cutting with small heat input always results in better finish of cut surface. Uslan.I [4] has investigated the influence of laser power and cutting speed variations on the kerf width size. A lump parameter analysis is introduced when predicting the kerf width size and an experiment is conducted to measure the kerf size and its variation during the cutting process. He has found that the workpiece surface influences significantly the kerf width size. He has also shown that the variation in the power intensity results in considerable variation in the kerf size during the cutting, which is more pronounced at lower intensities. Zhang et al [5] have proposed a synthetic evaluation method for laser cutting quality. B S Yilbas et al [6] using a CO<sub>2</sub> laser with variable pulse frequency and Oxygen, as assisting gas, at different pressures have investigated the cutting process. SEM and X ray diffraction are carried out to obtain micrographs and oxide compounds formed in the dross. They have found that the liquid layer thickness increases with increasing laser output power and reduces with increasing assisting gas velocity. The mechanics of dross formation has been studied by using the relation between kinetic energy of the melt film and the local temperature. Striation produced during the laser cutting affects the surface roughness, appearances and geometry of laser cut products. Lin Li, M. Sobih and P.L. Crouse [7] have given a theoretical model to predict the critical cutting speed at which striation-free cutting takes place. It is also observed that at cutting speeds above the critical cutting speed, striation reappears and surface roughness increases with the cutting speed.

In this present paper, two output responses are taken such as kerf taper and surface roughness have been optimized simultaneously during continues wave CO<sub>2</sub> laser beam cutting of AISI 9255 spring steel using approach of Topsis method. The control factors taken as laser power, gas pressure, focal distance and cutting speed. The plate material of AISI 9255 spring steel having thickness of 8 mm is taken into consideration. Firstly, Experiments have been performed on AISI 9255 spring steel work piece based upon Taguchi experimental design L<sub>27</sub> orthogonal array. The results obtained from Taguchi-based experiment have been used in Topsis for finding optimal solutions.

## II. EXPERIMENTATION

The experiments are conducted on High power CO<sub>2</sub> Laser Machining centre model no Trumatic L6050, made by GSI group laser division, United Kingdom which is available with M/s. Meera Laser Solutions (I) PVT. LTD. Chennai, Tamilnadu. The maximum average power produced at laser is 3200W. In this research profile cutting of AISI 9255 spring steel is carried out at by varying the input parameters. The chemical composition of the material is given in Table I.

Table I: Chemical Composition Of Aisi 9255 Spring Steel

| %   | C    | Cr   | Si   | Mn   | P    | V    | S    | Fe      |
|-----|------|------|------|------|------|------|------|---------|
| Min | 0.45 | 0.80 | 0    | 0.50 | 0    | 0    | 0    | Balance |
| max | 0.55 | 1.20 | 0.50 | 0.80 | 0.06 | 0.15 | 0.06 |         |

### A. Experimental setup

The CO<sub>2</sub> Laser Beam cutting equipment used for the present work is shown in Fig. 2 & Fig. 3. Fig. 2 shows the 3-axes CNC assisted Laser cutting unit, control unit and the fixture to locate the work piece. Fig. 2 shows the LBC machine showing Laser head in ready-to-start position. Fig. 3 shows the running position of the machine and the laser beam coming from the laser head can also be seen. The conditions at which the experiments were carried out are detailed in Table II. Based on the literature survey and the trial experiments, it was found that the process parameters such as Laser power, cutting speed, gas pressure, and focal distance have



significant effect on cut edge quality such as surface roughness and taper kerf. In the present work, surface roughness and taper kerf are considered as the decision variables and trial samples of square profile cutting with the dimensions of 10 x 10 mm are performed by varying one of the process variables to determine the working range of each process variable.



Fig 2: The CO2 laser-machining center (Trumatic L6050)

Fig. 3: CO<sub>2</sub> Laser Machining process

Table II: Experimental Conditions

| Factors        | Units  | Levels |      |      |
|----------------|--------|--------|------|------|
|                |        | I      | II   | III  |
| Power          | KW     | 1.6    | 1.8  | 2.0  |
| Cutting Speed  | mm/sec | 4000   | 4250 | 4500 |
| Gas Pressure   | Bar    | 2.0    | 2.5  | 3.0  |
| Focal Distance | mm     | 1      | 1.1  | 1.2  |

### B. Design of Experiments

Design of experiments (DOE) is used to find out the effect of different process response parameters on different control factors and for getting the relation between them. For giving the minimum no of experimental runs, we will get the required amount of information it will save the machine time and cost of the experiment. In taguchi method the experiments are performed as per the standard orthogonal arrays (OA). The selection of orthogonal array depends on the total degree of freedom (DOF). In the present investigation to check the DOFs in the experimental design for the three-level test, the four main factors take 8 ( $4 \times (3-1)$ ) DOFs. For three second order interactions ( $A \times B$ ,  $A \times C$ ,  $B \times C$ ) is 16 ( $4 \times (3-1) \times (3-1)$ ) and the total DOFs required is 24 (8+16). Here the L<sub>27</sub> OA (DOF: 26) has been selected. The design of experiments is given in Table III to run the experiments.

### III. EXPERIMENTAL RESULTS AND DISCUSSIONS

The experimental results for process responses such as kerf taper angle and surface roughness are presented in Table III.

Table iii. Experimetal run along with the output response values

| S. No | Power (KW) | Cutting speed (mm/sec) | Gas Pressure (Bars) | Focal Distance (mm) | Kerf taper (degree) | Surface roughness (µm) |
|-------|------------|------------------------|---------------------|---------------------|---------------------|------------------------|
| 1     | 1.6        | 4000                   | 2.0                 | 1.0                 | 0.303               | 5.851                  |
| 2     | 1.6        | 4000                   | 2.5                 | 1.1                 | 0.758               | 5.710                  |
| 3     | 1.6        | 4000                   | 3.0                 | 1.2                 | 0.761               | 4.398                  |
| 4     | 1.6        | 4250                   | 2.0                 | 1.1                 | 0.311               | 5.951                  |
| 5     | 1.6        | 4250                   | 2.5                 | 1.2                 | 0.521               | 3.317                  |
| 6     | 1.6        | 4250                   | 3.0                 | 1.0                 | 0.697               | 5.024                  |
| 7     | 1.6        | 4500                   | 2.0                 | 1.2                 | 0.306               | 5.340                  |
| 8     | 1.6        | 4500                   | 2.5                 | 1.0                 | 0.711               | 5.602                  |
| 9     | 1.6        | 4500                   | 3.0                 | 1.1                 | 0.820               | 6.083                  |
| 10    | 1.8        | 4000                   | 2.0                 | 1.1                 | 0.511               | 2.970                  |
| 11    | 1.8        | 4000                   | 2.5                 | 1.2                 | 0.660               | 2.756                  |
| 12    | 1.8        | 4000                   | 3.0                 | 1.0                 | 0.702               | 2.920                  |
| 13    | 1.8        | 4250                   | 2.0                 | 1.2                 | 0.6365              | 4.457                  |
| 14    | 1.8        | 4250                   | 2.5                 | 1.0                 | 0.465               | 2.582                  |
| 15    | 1.8        | 4250                   | 3.0                 | 1.1                 | 0.881               | 2.849                  |
| 16    | 1.8        | 4500                   | 2.0                 | 1.0                 | 0.725               | 4.156                  |
| 17    | 1.8        | 4500                   | 2.5                 | 1.1                 | 0.577               | 2.368                  |
| 18    | 1.8        | 4500                   | 3.0                 | 1.2                 | 0.625               | 2.125                  |
| 19    | 2.0        | 4000                   | 2.0                 | 1.2                 | 0.780               | 2.055                  |
| 20    | 2.0        | 4000                   | 2.5                 | 1.0                 | 0.819               | 2.455                  |
| 21    | 2.0        | 4000                   | 3.0                 | 1.1                 | 0.502               | 2.551                  |
| 22    | 2.0        | 4250                   | 2.0                 | 1.0                 | 0.711               | 1.309                  |
| 23    | 2.0        | 4250                   | 2.5                 | 1.1                 | 0.582               | 1.034                  |
| 24    | 2.0        | 4250                   | 3.0                 | 1.2                 | 0.565               | 1.584                  |
| 25    | 2.0        | 4500                   | 2.0                 | 1.1                 | 0.779               | 1.570                  |
| 26    | 2.0        | 4500                   | 2.5                 | 1.2                 | 0.661               | 3.709                  |
| 27    | 2.0        | 4500                   | 3.0                 | 1.0                 | 0.571               | 1.439                  |

A. *Topsis method*

TOPSIS stands for technique for order preference by similarity to ideal solution. This method was developed by Hwang and Yoon in the year 1995. Technique for order preference by similarity to ideal solution (TOPSIS) is based on the idea that the chosen alternative should have the shortest distance from the positive ideal solution and on the other side the farthest distance of the negative ideal solution. The ideal solution is a hypothetical solution for which all attribute values correspond to the minimum attribute values in the data base. TOPSIS thus gives a solution that is not only closest to the hypothetically best but also farthest from the hypothetically worst. The steps followed for the TOPSIS in the present research work are given below.

1) Step 1: Decision matrix is normalized by using the following equation:

$$r_{ij} = \frac{a_{ij}}{\sqrt{\sum_{i=1}^m a_{ij}^2}} \text{ ----- Equ. (1)}$$

where  $i = 1 \dots m$  and  $j = 1 \dots n$ .  $a_{ij}$  represents the actual value of the  $i^{\text{th}}$  value of  $j^{\text{th}}$  experimental run and  $r_{ij}$  represents the corresponding normalized value. The normalized values of kerf taper and surface roughness are presented in Table IV.

2) Step 2: Weight for each response is calculated. Here, equal weightage is given to all the responses. Therefore,  $w_j = 0.50$ . The weights for all the responses are given in Table V.

$$V_{ij} = W_i \times r_{ij} \text{ ----- Equ. (2)}$$

where  $i = 1 \dots m$  and  $j = 1 \dots n$ .  $w_j$  represents the weight of the  $j^{\text{th}}$  attribute or criteria.

3) Step 3: In this step, the worst alternative ( $t_{wj}$ ) and the best alternative ( $t_{bj}$ ) are determined from the weighted normalized values ( $t_{ij}$ ). These values are used to determine the separation measures. Table VI shows the Best and worst values of output parameters.

Table IV: Normalized Values Of Surface Roughness And Kerf Taper

| S. No | Power (KW) | Cutting speed (mm/sec) | Gas Pressure (Bars) | Focal Distance (mm) | Normalized Values |                   |
|-------|------------|------------------------|---------------------|---------------------|-------------------|-------------------|
|       |            |                        |                     |                     | Kerf taper        | Surface roughness |
| 1     | 1.6        | 4000                   | 2.0                 | 1.0                 | 0.090             | 1.743             |
| 2     | 1.6        | 4000                   | 2.5                 | 1.1                 | 0.226             | 1.701             |
| 3     | 1.6        | 4000                   | 3.0                 | 1.2                 | 0.227             | 1.310             |
| 4     | 1.6        | 4250                   | 2.0                 | 1.1                 | 0.093             | 1.773             |
| 5     | 1.6        | 4250                   | 2.5                 | 1.2                 | 0.155             | 0.988             |
| 6     | 1.6        | 4250                   | 3.0                 | 1.0                 | 0.208             | 1.497             |
| 7     | 1.6        | 4500                   | 2.0                 | 1.2                 | 0.091             | 1.591             |
| 8     | 1.6        | 4500                   | 2.5                 | 1.0                 | 0.212             | 1.669             |
| 9     | 1.6        | 4500                   | 3.0                 | 1.1                 | 0.244             | 1.812             |
| 10    | 1.8        | 4000                   | 2.0                 | 1.1                 | 0.152             | 0.885             |
| 11    | 1.8        | 4000                   | 2.5                 | 1.2                 | 0.197             | 0.821             |
| 12    | 1.8        | 4000                   | 3.0                 | 1.0                 | 0.209             | 0.870             |
| 13    | 1.8        | 4250                   | 2.0                 | 1.2                 | 0.190             | 1.328             |
| 14    | 1.8        | 4250                   | 2.5                 | 1.0                 | 0.139             | 0.769             |
| 15    | 1.8        | 4250                   | 3.0                 | 1.1                 | 0.262             | 0.849             |
| 16    | 1.8        | 4500                   | 2.0                 | 1.0                 | 0.216             | 1.238             |
| 17    | 1.8        | 4500                   | 2.5                 | 1.1                 | 0.172             | 0.705             |
| 18    | 1.8        | 4500                   | 3.0                 | 1.2                 | 0.186             | 0.633             |
| 19    | 2.0        | 4000                   | 2.0                 | 1.2                 | 0.232             | 0.612             |
| 20    | 2.0        | 4000                   | 2.5                 | 1.0                 | 0.244             | 0.731             |
| 21    | 2.0        | 4000                   | 3.0                 | 1.1                 | 0.150             | 0.760             |
| 22    | 2.0        | 4250                   | 2.0                 | 1.0                 | 0.212             | 0.390             |
| 23    | 2.0        | 4250                   | 2.5                 | 1.1                 | 0.173             | 0.308             |
| 24    | 2.0        | 4250                   | 3.0                 | 1.2                 | 0.168             | 0.472             |
| 25    | 2.0        | 4500                   | 2.0                 | 1.1                 | 0.232             | 0.468             |
| 26    | 2.0        | 4500                   | 2.5                 | 1.2                 | 0.197             | 1.105             |
| 27    | 2.0        | 4500                   | 3.0                 | 1.0                 | 0.170             | 0.429             |

Table V: Weightage Values Of Surface Roughness And Kerf Taper

| S. No | Power (KW) | Cutting speed (mm/sec) | Gas Pressure (Bars) | Focal Distance (mm) | Weighted Decision matrix |                   |
|-------|------------|------------------------|---------------------|---------------------|--------------------------|-------------------|
|       |            |                        |                     |                     | Kerf taper               | Surface roughness |
| 1     | 1.6        | 4000                   | 2.0                 | 1.0                 | 0.0450                   | 0.8715            |
| 2     | 1.6        | 4000                   | 2.5                 | 1.1                 | 0.1130                   | 0.8505            |
| 3     | 1.6        | 4000                   | 3.0                 | 1.2                 | 0.1135                   | 0.6550            |
| 4     | 1.6        | 4250                   | 2.0                 | 1.1                 | 0.0465                   | 0.8865            |
| 5     | 1.6        | 4250                   | 2.5                 | 1.2                 | 0.0775                   | 0.4940            |
| 6     | 1.6        | 4250                   | 3.0                 | 1.0                 | 0.1040                   | 0.7485            |
| 7     | 1.6        | 4500                   | 2.0                 | 1.2                 | 0.0455                   | 0.7955            |
| 8     | 1.6        | 4500                   | 2.5                 | 1.0                 | 0.1060                   | 0.8345            |
| 9     | 1.6        | 4500                   | 3.0                 | 1.1                 | 0.1220                   | 0.9060            |
| 10    | 1.8        | 4000                   | 2.0                 | 1.1                 | 0.0760                   | 0.4425            |
| 11    | 1.8        | 4000                   | 2.5                 | 1.2                 | 0.0985                   | 0.4105            |
| 12    | 1.8        | 4000                   | 3.0                 | 1.0                 | 0.1045                   | 0.4350            |
| 13    | 1.8        | 4250                   | 2.0                 | 1.2                 | 0.0950                   | 0.6640            |
| 14    | 1.8        | 4250                   | 2.5                 | 1.0                 | 0.0695                   | 0.3845            |
| 15    | 1.8        | 4250                   | 3.0                 | 1.1                 | 0.1310                   | 0.4245            |
| 16    | 1.8        | 4500                   | 2.0                 | 1.0                 | 0.1080                   | 0.6190            |
| 17    | 1.8        | 4500                   | 2.5                 | 1.1                 | 0.0860                   | 0.3525            |
| 18    | 1.8        | 4500                   | 3.0                 | 1.2                 | 0.0930                   | 0.3165            |
| 19    | 2.0        | 4000                   | 2.0                 | 1.2                 | 0.1160                   | 0.3060            |
| 20    | 2.0        | 4000                   | 2.5                 | 1.0                 | 0.1220                   | 0.3655            |
| 21    | 2.0        | 4000                   | 3.0                 | 1.1                 | 0.0750                   | 0.3800            |
| 22    | 2.0        | 4250                   | 2.0                 | 1.0                 | 0.1060                   | 0.1950            |
| 23    | 2.0        | 4250                   | 2.5                 | 1.1                 | 0.0865                   | 0.1540            |
| 24    | 2.0        | 4250                   | 3.0                 | 1.2                 | 0.0840                   | 0.2360            |
| 25    | 2.0        | 4500                   | 2.0                 | 1.1                 | 0.1160                   | 0.2340            |
| 26    | 2.0        | 4500                   | 2.5                 | 1.2                 | 0.0985                   | 0.5525            |
| 27    | 2.0        | 4500                   | 3.0                 | 1.0                 | 0.0850                   | 0.2145            |

Table VI Best And Worst Values Of Output Parameters

| Output parameter  | V <sub>bj</sub> | V <sub>wj</sub> |
|-------------------|-----------------|-----------------|
| Kerf Taper        | 0.045           | 0.131           |
| Surface roughness | 0.154           | 0.906           |

4) Step 4: The separation of each alternative from positive ideal solution (PIS) and negative ideal solution (NIS) is calculated as

$$S_i^+ = \sqrt{\sum_{j=1}^n (V_{ij} - V_{bj})^2} \text{ ----- Equ. (3)}$$

$$S_i^- = \sqrt{\sum_{j=1}^n (V_{ij} - V_{wj})^2} \text{ ----- Equ. (4)}$$

where i = 1,2, 3, ... m, the separation measures for all experimental runs are given in Table VII.

TABLE VII SEPERATION MEASURE VALUES

| S. No | Power (KW) | Cutting speed (mm/sec) | Gas Pressure (Bars) | Focal Distance (mm) | Separation measures         |                             |
|-------|------------|------------------------|---------------------|---------------------|-----------------------------|-----------------------------|
|       |            |                        |                     |                     | S <sub>i</sub> <sup>+</sup> | S <sub>i</sub> <sup>-</sup> |
| 1     | 1.6        | 4000                   | 2.0                 | 1.0                 | 0.718                       | 0.093                       |
| 2     | 1.6        | 4000                   | 2.5                 | 1.1                 | 0.700                       | 0.058                       |
| 3     | 1.6        | 4000                   | 3.0                 | 1.2                 | 0.506                       | 0.252                       |
| 4     | 1.6        | 4250                   | 2.0                 | 1.1                 | 0.733                       | 0.087                       |
| 5     | 1.6        | 4250                   | 2.5                 | 1.2                 | 0.342                       | 0.415                       |
| 6     | 1.6        | 4250                   | 3.0                 | 1.0                 | 0.597                       | 0.160                       |
| 7     | 1.6        | 4500                   | 2.0                 | 1.2                 | 0.642                       | 0.140                       |
| 8     | 1.6        | 4500                   | 2.5                 | 1.0                 | 0.683                       | 0.076                       |
| 9     | 1.6        | 4500                   | 3.0                 | 1.1                 | 0.756                       | 0.009                       |
| 10    | 1.8        | 4000                   | 2.0                 | 1.1                 | 0.290                       | 0.467                       |
| 11    | 1.8        | 4000                   | 2.5                 | 1.2                 | 0.262                       | 0.497                       |
| 12    | 1.8        | 4000                   | 3.0                 | 1.0                 | 0.287                       | 0.472                       |
| 13    | 1.8        | 4250                   | 2.0                 | 1.2                 | 0.512                       | 0.245                       |
| 14    | 1.8        | 4250                   | 2.5                 | 1.0                 | 0.232                       | 0.525                       |
| 15    | 1.8        | 4250                   | 3.0                 | 1.1                 | 0.284                       | 0.482                       |
| 16    | 1.8        | 4500                   | 2.0                 | 1.0                 | 0.469                       | 0.288                       |
| 17    | 1.8        | 4500                   | 2.5                 | 1.1                 | 0.203                       | 0.555                       |
| 18    | 1.8        | 4500                   | 3.0                 | 1.2                 | 0.169                       | 0.591                       |
| 19    | 2.0        | 4000                   | 2.0                 | 1.2                 | 0.168                       | 0.600                       |
| 20    | 2.0        | 4000                   | 2.5                 | 1.0                 | 0.225                       | 0.541                       |
| 21    | 2.0        | 4000                   | 3.0                 | 1.1                 | 0.228                       | 0.529                       |
| 22    | 2.0        | 4250                   | 2.0                 | 1.0                 | 0.073                       | 0.711                       |
| 23    | 2.0        | 4250                   | 2.5                 | 1.1                 | 0.042                       | 0.753                       |
| 24    | 2.0        | 4250                   | 3.0                 | 1.2                 | 0.091                       | 0.672                       |
| 25    | 2.0        | 4500                   | 2.0                 | 1.1                 | 0.107                       | 0.672                       |
| 26    | 2.0        | 4500                   | 2.5                 | 1.2                 | 0.402                       | 0.355                       |
| 27    | 2.0        | 4500                   | 3.0                 | 1.0                 | 0.073                       | 0.693                       |

5) Step 5. The closeness coefficient of each alternative (CC<sub>i</sub>) is calculated as

$$CC_i = \frac{S_i^-}{S_i^+ + S_i^-} \text{ ----- Equ. (5)}$$

The closeness value to ideal solution values and corresponding values are given in Table VIII.



Table Viii Relational Closness Values And Their Ranks

| S. No | Power (KW) | Cutting speed (mm/sec) | Gas Pressure (Bars) | Focal Distance (mm) | Relative Closeness Value | Ranks |
|-------|------------|------------------------|---------------------|---------------------|--------------------------|-------|
| 1     | 1.6        | 4000                   | 2.0                 | 1.0                 | 0.40508                  | 27    |
| 2     | 1.6        | 4000                   | 2.5                 | 1.1                 | 0.37908                  | 11    |
| 3     | 1.6        | 4000                   | 3.0                 | 1.2                 | 0.37864                  | 9     |
| 4     | 1.6        | 4250                   | 2.0                 | 1.1                 | 0.40961                  | 26    |
| 5     | 1.6        | 4250                   | 2.5                 | 1.2                 | 0.37850                  | 4     |
| 6     | 1.6        | 4250                   | 3.0                 | 1.0                 | 0.37861                  | 8     |
| 7     | 1.6        | 4500                   | 2.0                 | 1.2                 | 0.39061                  | 23    |
| 8     | 1.6        | 4500                   | 2.5                 | 1.0                 | 0.37949                  | 14    |
| 9     | 1.6        | 4500                   | 3.0                 | 1.1                 | 0.38247                  | 17    |
| 10    | 1.8        | 4000                   | 2.0                 | 1.1                 | 0.37845                  | 1     |
| 11    | 1.8        | 4000                   | 2.5                 | 1.2                 | 0.37929                  | 12    |
| 12    | 1.8        | 4000                   | 3.0                 | 1.0                 | 0.37948                  | 13    |
| 13    | 1.8        | 4250                   | 2.0                 | 1.2                 | 0.37855                  | 6     |
| 14    | 1.8        | 4250                   | 2.5                 | 1.0                 | 0.37846                  | 2     |
| 15    | 1.8        | 4250                   | 3.0                 | 1.1                 | 0.38267                  | 18    |
| 16    | 1.8        | 4500                   | 2.0                 | 1.0                 | 0.37858                  | 7     |
| 17    | 1.8        | 4500                   | 2.5                 | 1.1                 | 0.37901                  | 10    |
| 18    | 1.8        | 4500                   | 3.0                 | 1.2                 | 0.38008                  | 15    |
| 19    | 2.0        | 4000                   | 2.0                 | 1.2                 | 0.38398                  | 21    |
| 20    | 2.0        | 4000                   | 2.5                 | 1.0                 | 0.38283                  | 20    |
| 21    | 2.0        | 4000                   | 3.0                 | 1.1                 | 0.37848                  | 3     |
| 22    | 2.0        | 4250                   | 2.0                 | 1.0                 | 0.39247                  | 24    |
| 23    | 2.0        | 4250                   | 2.5                 | 1.1                 | 0.39741                  | 25    |
| 24    | 2.0        | 4250                   | 3.0                 | 1.2                 | 0.38122                  | 16    |
| 25    | 2.0        | 4500                   | 2.0                 | 1.1                 | 0.38957                  | 22    |
| 26    | 2.0        | 4500                   | 2.5                 | 1.2                 | 0.37853                  | 5     |
| 27    | 2.0        | 4500                   | 3.0                 | 1.0                 | 0.38278                  | 19    |

#### IV. CONCLUSIONS

The scope of present paper was the optimization of process parameters in laser beam machining of AISI 9255 spring steel using TOPSIS Method. The process parameters examined in this investigation are cutting speed, laser power, gas pressure and focal distance. The following conclusions are made.

- A. The optimized process parameter setting is laser power 1.8 KW, cutting speed of 4000 mm/sec, gas pressure of 2.0 bars and 1.1 mm focal distance.
- B. The results obtained in the analysis are validated and the results based on turning process responses can be effectively improved.



- C. The proposed experimental and statistical approach is simple, useful, and a reliable methodology to optimize laser welding parameters efficiently. In future, this method can be used to optimize and improve other process parameters. Also, this method can be extended to study other machining processes.

#### REFERENCES

- [1] B.S.Yilbas A., F.M.Arif, B.J.Abdul Aleem,, “Dross formation during laser cutting process”, J. Phys. D: Appl. Phys. 39,1451-1461 [2006]
- [2] Dayana Espinal and Aravinda Kar (2000) , “Thermochemical modeling of oxygen assisted laser cutting”, Journal of Laser Applications, February, Volume 12, Issue 1, pp 16 – 22
- [3] Asano,Hiroshi, Suzuki,Jippe,Kawakami,Eguchi(2003), “Selection of parameters on laser cutting mild steel plates taking account of some manufacturing purposes”, Fourth International symposium on laser precision microfabrication. Proceedings of SPIE, Volume 5063, pp 418-425.
- [4] Uslan.I (2005), “CO2 laser cutting: kerf width variation during cutting”, Proceedings of the I MECH E Part B Journal of Engineering Manufacture, Number B8, August 2005, pp. 571-578(8).
- [5] Lawrence Yao, Hongquiang Chen and Wenwu Zhang (2004), “Time scale effects in laser material removal”, International Journal of Advanced Manufacturing Technology
- [6] B.S.YilbasA., F.M.Arif, B.J.Abdul Aleem, “Laser welding of low carbon steel and thermal stress analysis”, Optics & Laser Technology, Volume 42, Issue 5, July 2010, Pages 760-768
- [7] Lin Li, M. Sobih and P.L. Crouse (2007), “Striation free Laser Cutting of Mild Steel”, Sheets, CIRP Annals of Manufacturing Technology, Volume 56, Issue 1, Pages 193-196.



10.22214/IJRASET



45.98



IMPACT FACTOR:  
7.129



IMPACT FACTOR:  
7.429



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24\*7 Support on Whatsapp)